





Article

Cement-Bonded Particleboards with Banana Pseudostem Waste: Physical Performance and Bio-Susceptibility

Lina Nunes ^{1,2,*} , Eleonora Cintura ^{1,3,4} , João L. Parracha ^{1,4} , Bruno Fernandes ³, Vitor Silva ³ and Paulina Faria ^{3,4} 

¹ National Laboratory for Civil Engineering, Avenida do Brasil 101, 1700-066 Lisbon, Portugal; ecintura@lnec.pt (E.C.); jparracha@lnec.pt (J.L.P.)

² CE3C, University of the Azores, 9700-042 Angra do Heroísmo, Portugal

³ Department of Civil Engineering, FCT, NOVA University of Lisbon, 2829-516 Caparica, Portugal; bma.fernandes@campus.fct.unl.pt (B.F.); vmd.silva@fct.unl.pt (V.S.); paulina.faria@fct.unl.pt (P.F.)

⁴ CERIS, Civil Engineering Research and Innovation for Sustainability, IST, 1049-001 Lisbon, Portugal

* Correspondence: linanunes@lnec.pt

Abstract: This article evaluates the relevant properties of cement-bonded particleboards (CBPB) made with a portion of maritime pine (*Pinus pinaster*) particles replaced with an agricultural waste, banana pseudostem (*Musa* sp.). The industrial production of CBPB was simulated in the laboratory based on a reference composition defined by a manufacturing company. Test specimens were produced assuming 0%, 25%, 50% and 75% partial replacement of wood particles with banana pseudostem fibres. Some physical properties (bulk density, thermal conductivity, and dimensional stability) and the mould susceptibility of the different variables were assessed. Results show that the thermal conductivity of the boards increased with the banana fibre proportion and ranged between 0.233 W/(m.K) and 0.279 W/(m.K). The bulk density values generally increased with the banana fibre proportion and ranged between 1754–1995 kg/m³, being the highest value obtained for B50 (equal weight proportion of wood particles and banana fibres). Specimens with a higher percentage of banana fibres have reduced thickness resulting from swelling, ranging between 0.38% and 0.11% (for 0% and 75% of banana fibres, respectively). CBPBs with unsanded surfaces seem to be unsusceptible to mould development, whereas those with sanded surfaces, simulating wearing, show some bio-susceptibility. Mould development increases with the proportion of banana fibre. The results highlight the need for regular maintenance of the particleboards, thus avoiding surface wear over time and resulting in the exposure of the wood particles and/or banana fibres to the outside environment.

Keywords: bio-wastes; banana pseudostem fibres; maritime pine particles; physical properties; mould susceptibility.



Citation: Nunes, L.; Cintura, E.; Parracha, J.L.; Fernandes, B.; Silva, V.; Faria, P. Cement-Bonded Particleboards with Banana Pseudostem Waste: Physical Performance and Bio-Susceptibility. *Infrastructures* **2021**, *6*, 86. <https://doi.org/10.3390/infrastructures6060086>

Academic Editor: Md. Safiuddin

Received: 17 May 2021

Accepted: 11 June 2021

Published: 13 June 2021

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Cement-bonded particleboards (CBPB) are construction materials that are being largely used both in new construction and for the rehabilitation/retrofitting of existing buildings. This article is focused on the durability and degradability of coating materials applied in buildings, namely, to assess the relevant properties of innovative CBPB when raw wood particles were partially replaced with banana tree wastes.

Recently, renewed attention has been given to the use of cement-bonded particleboards (CBPB), particularly with added lignocellulosic wastes [1–5] or alternative wood species [6,7] for numerous applications, such as interior walls, external cladding surfaces, ceiling panels or decorative applications [8,9]. However, it is important to ensure that this replacement does not increase in-service problems and that the in situ behavior is validated.

The conventional composite boards are made of a mixture of wood particles (approximately 23%), typically from waste wood and Portland cement (approximately 62%), additives (e.g., pigments and hardeners, approximately 4.5%), and water (approximately 10.5%) [10]. The use of cement in CBPB gives the final product good fire performance and biological resistance, whereas the use of wood-based products favors the thermal and acoustic insulation properties [11,12]. The compatibility between the two materials depends on several characteristics like wood species, production process, and chemical characteristics [13,14]. One important element to be considered is the polysaccharides (sugar content) that can inhibit cement setting time, thus contributing to lower bonding of wood with cement [4,15]. Nevertheless, this problem can be overcome by using chemical accelerators such as calcium chloride, which will decrease the hydration time of the boards, thus increasing compatibility between the wood and cement [16].

Over the last decades, several studies have been focused on the possibility of using residues of vegetal origin as building composites [17–20]. This practice contributes both to the manufacture of products with lower embodied energy and to the circular economy in the construction sector. Considering the environmental problems caused by the disposal of some biowastes [21,22], incorporating lignocellulosic residues in CBPB composition can be an efficient solution to limit this issue [23]. For example, Rocha Almeida et al. [24] analyzed the possibility of producing CBPB by adding coconut shells from babaçu (*Orbignya* sp.), a palm tree from Brazil, demonstrating that this natural material could improve the mechanical resistance and dimensional stability of the boards. Cabral et al. [25] considered the production of CBPB using Jerusalem artichoke (*Helianthus tuberosus*) stalk particles and found lower values of thickness swelling and water absorption of the boards when compared to those values reported in the literature. Rana et al. [4] studied the effects of the addition of chemical additives and magnesium chloride on the setting time of jute stick CBPB and concluded that the additives can help with the improvement of the physical and mechanical properties of the boards. Cavdar et al. [26] concluded that paper-mill sludge can be used in CBPB formulation, up to 20% of total composite weight, depending on the type of sludge used (grey, black, or a mixture of grey and black). Nazerian and Sadeghiipana [27] investigated the hydration behavior and physical properties of CBPB by incorporating wheat straw and poplar wood at various ratios. They concluded that, compared with control samples, both the hydration time and compressive strength significantly decline along with increases in lignocellulosic materials quantity. Ferrandez-Villena et al. [3] considered the production of CBPB with Canary Islands palm (*Phoenix canariensis* Ch.) trunks and obtained a low thermal conductivity for the boards ($0.054 \text{ W.m}^{-1}.\text{K}^{-1}$), as well as a good mechanical performance. In parallel, Omoniyi and Olorunnisola [28] examined the effects of methods of manufacture, fiber contents and pretreatment on the physico-mechanical properties of bagasse-reinforced cement composites and concluded that the interaction of these variables had significant effects on the sorption and the strength properties of the composites.

Finally, Ogunsile et al. [29] and Nadhari et al. [30] evaluated the influence of the addition of banana stalk particles (*Musa* sp.) on the physical properties and dimensional stability of CBPB. Ogunsile et al. [29] demonstrated that both thickness swelling and water absorption can increase with higher fibre content, whereas Nadhari et al. [30] found that CBPB specimens formulated with banana stalk treated at 121°C obtained higher values of thickness swelling and water absorption in comparison with those formulated with stalk with no pre-treatment and treated at 111°C or 131°C . However, Nadhari et al. [30] assumed the same banana fibre content for all tested boards, and the study of Ogunsile et al. [29] does not refer the percentage of banana stalk fibres replacing wood particles for each CBPB formulation. Moreover, the biological susceptibility of the boards was not considered by the authors.

Banana plants (*Musa* sp.) are native to Asia but grow in many different environments. They are adaptable to mixed farming and are grown in large areas in tropical and sub-tropical areas [31]. Its production takes place mainly in Asia (56%), Latin America (26%)

and Africa (15%) [32]. According to FAO [33], it is the main crop in the world, with rising production of 60 million tons in 2000-2002 to 116 million tons in 2017-2019. The production cycle lasts only two years leading to a high volume of waste materials derived from this crop [34,35]. Therefore, the volume of waste produced can be reused for the development of CBPB and other building products.

Focused on the objective of the circular economy, this article studies the viability of producing CBPB with increasing proportions of maritime pine (*Pinus pinaster*) particles replaced with an agricultural waste, banana pseudostem. The industrial production of CBPB was simulated in the laboratory and based on a reference composition defined by a CBPB manufacturing company. Test specimens were produced by replacing wood particles with banana pseudostem fibers in different percentages: 0%, 25%, 50%, and 75%. Some physical properties and the bio-susceptibility of the different specimens were assessed with the aim of determining the influence of the biowaste on panels' features. Considering the good thermal insulation properties of many natural fibers, the insulation capacity of the specimens was studied by analyzing their thermal conductivity and loose bulk density. An additional objective of the present study was to evaluate the immediate (unsanded surfaces, replicating new boards) and long-term (sanded surfaces, replicating weathered boards) mould susceptibility of the boards, as well as their dimensional stability. Ultimately, this work aims at evaluating the feasibility of producing these new boards, thus contributing to the reduction of waste to manage.

2. Materials and Methods

2.1. Materials

2.1.1. Banana Pseudostem Waste

Banana (*Musa* sp.) pseudostem waste was collected from Ribeira Brava municipality, on Madeira Island, Portugal, and first dried in open air. Then, the fibres were manually cut until reaching dimensions of a few centimeters and later, was milled in a laminar mill to reduce the particle size to dimensions of less than 10 mm. The particle size distribution of banana fibres (Figure 1) had been determined previously [36]. Loose bulk density was measured according to EN 1097-3 (1998) [37], both for particles above 10 mm and for the ones below 10 mm. The results are 70 g/m³ and 130 g/m³, respectively.

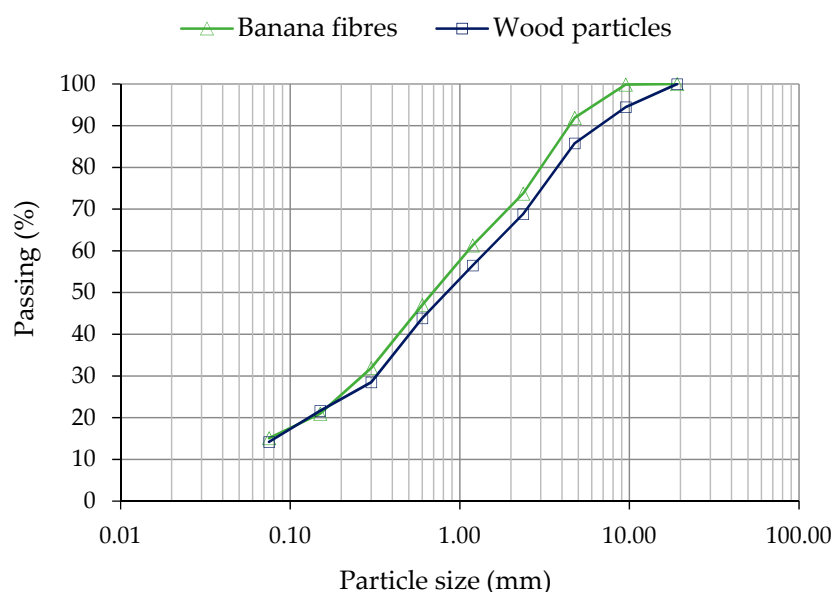


Figure 1. Particle size distribution of the banana fibres and the wood particles (adapted from [36]).

2.1.2. Maritime Pine Particles

Maritime pine particles were provided by the CBPB manufacturing company. Figure 1 shows the particle size distribution of pine particles. Loose bulk density was measured according to EN 1097-3 (1998) [37]. Particles above 10 mm had a measured density of 70 g/m³, while for particles below 10 mm, the measured density was 150 g/m³.

2.1.3. Binder and Additives

Portland cement type II (CEM II AL-L 42.5R) was used as a binder, according to a conventional composition [10]. Aluminium sulphate (Al₂(SO₄)₃) and sodium silicate (Na₂SiO₃) were both used as additives to improve the compatibility among wood, cement, and water and to reduce setting time [4,38].

2.1.4. Board Manufacturing

CBPBs were produced assuming 0%, 25%, 50% and 75% (by weight) partial replacement of wood particles with banana pseudostem fibres (Table 1). First, dried wood particles and banana fibres were uniformly mixed following the defined proportions in different containers for each composition. The wood particles+banana fibres:cement:water weight ratio was defined and maintained, as well as the percentage by weight of cement (approximately 62%) and a mixed solution of aluminium sulphate and sodium silicate. Thus, the only difference between the samples was the percentage of wood and banana fibres. The mixture was then blended for 3 min a homogeneous material was obtained (Figure 2a). After that, the material was placed into the moulding form (Figure 2b). Care was taken to ensure that the external surfaces of the board samples were produced with finer material, while the interior thickness had an increased content of coarse fibres. As shown in previous studies [39,40], particle-size distribution has a strong influence on the physical and mechanical properties of the boards. It is known that larger particles in the central core (lower density) ensure the better compaction of the boards and improve their mechanical properties. In turn, smaller particles (higher density) in the external layers improve the surface quality and bending properties of the boards [39,40]. Subsequently, the moulds were removed, and samples pressed at 24 MPa for 10 h (Figure 2c) in an oven (50 °C, 50% RH).

Table 1. Mix percentages of the boards (by weight).

Samples	Banana Fibres [%]	Wood Particles [%]
B0	0	100
B25	25	75
B50	50	50
B75	75	25

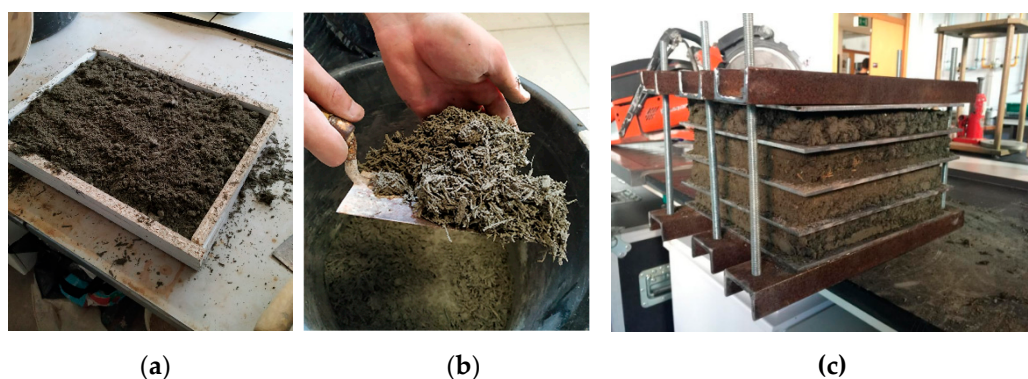


Figure 2. CBPB manufacturing: (a) homogeneous material obtained after 3 min of blending; (b) material placed into the molding; (c) layers of material before being pressed at 24 MPa.

Four boards (B0, B25, B50, B75) of 300 mm × 300 mm, with an approximate thickness of 13 mm, were produced, demoulded, and conditioned in a climatic chamber at 23 °C and 45% RH for 7 days. The bulk density of the panels was not controlled during the board manufacturing and was later determined by the ratio between the mass and the volume of the boards (EN 323, 1993 [41]), as reported in Section 2.2. Finally, boards were placed into an oven for 10 h with 70 °C and 45% RH for complete drying.

2.2. Methods

All tests were performed after 10 h of drying at 70 °C and 45% relative humidity (RH) for mass stabilization (Section 2.1.4), and after the board samples were cut for several specimens, based on the specimen dimensions required for each test, defined by CBPB standards. Table 2 summarizes the tests performed, as well as the sampling and respective dimensions.

Table 2. Tests performed, sampling, dimensions and standards followed.

Properties		Specimens	Area of the Specimen [mm ²]	Standards
Physical properties	Thermal conductivity	3 specimens (1 measurements per specimen) × 4 compositions (B0, B25, B50, B75)	50 × 50	EN 12664 (2001) [42]
	Bulk density	4 specimens × 4 compositions	50 × 50	EN 323 (1993) [41]
	Dimensional stability (water immersion)	4 specimens × 4 compositions	50 × 50	EN 317 (1993) [43]
Biological susceptibility to moulds		3 specimens × 4 compositions × 2 conditions (sanded (p); unsanded (u))	45 × 45	ASTM D5590-17 (2017) [44] and ASTM C1338-19 (2019) [45]

Thermal conductivity measurements, using a heat transfer analyzer ISOMET 2014 and a 60 mm diameter contact probe API 210416, with a measurement range of 0.03–0.6 W/(m.K), were performed for each composition. The test was performed in laboratory equilibrium conditions (T = 23 °C, 45% RH), and thermal conductivity was measured in three specimens of each composition (1 measurement per specimen).

The bulk density of each specimen was determined by the ratio between the mass and the volume of the specimen, based on EN 323 (1993) [41].

The dimensional stability of each specimen was determined by measuring the thickness swelling. Specimens of each composition cut from the original CBPB were completely immersed in water at a temperature of 20 ± 1 °C for 24 h (EN 317 (1993) [43]). Thickness swelling was obtained using Equation (1).

$$\text{Thickness swelling (\%)} = \frac{(T_2 - T_1)}{T_1} \times 100, \quad (1)$$

In the above equation, T₁ (mm) is the initial average thickness and T₂ (mm) is the final average thickness after water immersion for 24 h.

A method adapted from ASTM D5590-17 (2017) [44] and ASTM C1338-19 (2019) [45], previously described by Parracha et al. [46], was used to evaluate the biological susceptibility of the CBPB to moulds. Six specimens of each composition (B0, B25, B50, B75) were tested considering two different conditions: sanded and unsanded surfaces (Table 2). The surface of half of the specimens (B0p, B25p, B50p, B75p) was sanded twice with Dexter Wood GR120 sanding paper (Figure 3b) removing less than 1 mm of the surface, just enough to expose wood or banana particles. The objective was to simulate some deterioration of the surface layer caused by aging or other events (e.g., human action), thus exposing the wood/banana particles and possibly influencing the biological susceptibility results.

The other three specimens were tested with unsanded surfaces (B0u, B25u, B50u, B75u) (Figure 3a), simulating new boards.

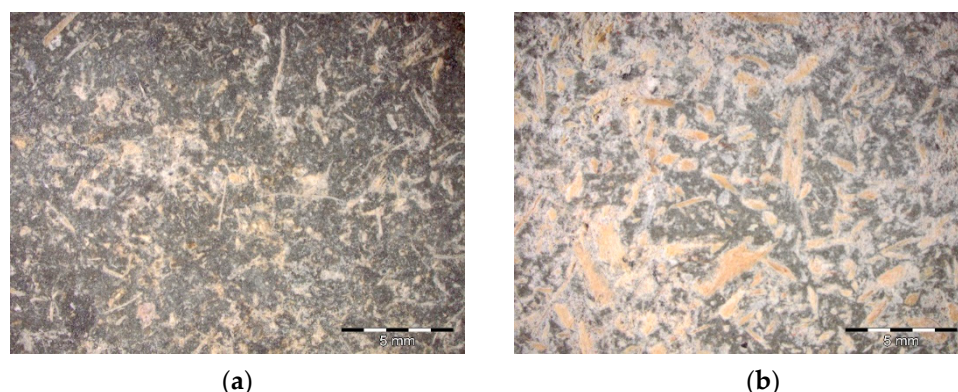


Figure 3. Examples of CBPB test specimens before fungal exposure (a) B50u unsanded; (b) B50p sanded.

Specimens were inoculated with a mixed spore suspension of *Aspergillus niger* and *Penicillium funicullosum* that were selected as representative biodeterioration agents. All specimens were steam-sterilized for 20 min in an autoclave and placed on test flasks previously prepared with culture media (4% malt, 2% agar). Afterwards, 2 mL of spore suspension was uniformly applied on the specimens' surface and culture media, and then the flasks were incubated for four weeks in a culturing chamber ($T = 22 \pm 1^\circ\text{C}$, $70 \pm 5\%$ RH).

Three control specimens of maritime pine with similar dimensions were used to verify the viability of the fungal strains, thus allowing the validation of the test. All of the specimens (CBPB and controls) were visually assessed each week following the scale defined in Table 3. At the end of the four-week testing period, specimens were removed from the flasks, and the percentage of the contaminated surface was evaluated using a stereo microscope Olympus B061.

Table 3. Rate of mould growth (ASTM D 5590-17, 2017) [43].

Rating	Description	Contaminated Surface [%]
0	None	0
1	Traces of growth	<10
2	Light growth	10 to 30
3	Moderate growth	30 to 60
4	Heavy growth	>60

3. Results and Discussion

3.1. Thermal Conductivity

Figure 4 presents the results of thermal conductivity. The highest value of thermal conductivity was obtained for composition B75 ($0.279 \text{ W}/(\text{m.K})$), which was very close to composition B50 ($0.269 \text{ W}/(\text{m.K})$), while the lowest was for specimen B0 ($0.233 \text{ W}/(\text{m.K})$), although within the variation of B25. It can be observed that thermal conductivity increases with the proportion of banana fibres that replace wood particles.

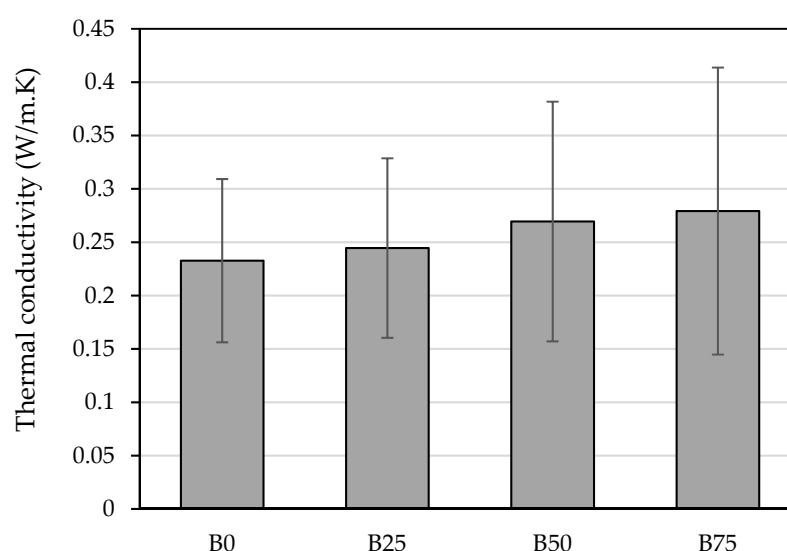


Figure 4. Average thermal conductivity results.

Comparing the values of the present study with the literature, it is possible to say that the thermal conductivity of the presently produced CBPB samples is not only lower than that of concrete boards, with values of 1.52 ± 0.03 W/(m.K) but also lower than some wood particleboards, with values of 0.29 ± 0.01 W/(m.K) [38,47]. However, Park et al. [48] obtained lower thermal conductivity values ranging between 0.074 W/(m.K) and 0.108 W/(m.K) for boards made of wood, cement, and lime, whereas Wang et al. [49] reported values of 0.10 W/(m.K) and 0.14 W/(m.K) for cement-bonded particleboards with grapevine stalk particles.

3.2. Bulk Density

The results of bulk density are shown in Figure 5, with completely dried cut specimens (Table 2). Specimens B50 and B75 present the highest average bulk densities (1995 kg/m^3 and 1948 kg/m^3 , respectively). As can be seen, the values of bulk density increase with the proportion of banana fibres, which indicates the greater compactness of the CBPB. This can be justified by the different loose bulk density of the wood in comparison to the banana pseudostem fibres, corresponding to different added volumes when wood was replaced by banana tree fibres. For maritime pine, bulk densities ranging between $530\text{--}600 \text{ kg/m}^3$ have been presented [50], whereas Idicula et al. [51] obtained a value of 1350 kg/m^3 for banana fibre. Part of this difference can be justified by the filler resulting from the banana pseudostem milling that can be observed by the particle size distribution of this material (Figure 1). Specimens with 0% banana tree fibres (B0) obtain the lowest bulk density (1754 kg/m^3), corresponding to a decrease of 21 kg/m^3 when compared to the highest value, obtained for B50 specimens.

Rocha Almeida et al. [24] obtained lower values of bulk density, in the range of $1200\text{--}1400 \text{ kg/m}^3$, for babaçu coconut shell CBPB, while Macêdo et al. [52] also obtained lower values of bulk density, between 1330 kg/m^3 and 1557 kg/m^3 , for CBPB produced with the waste wood of six Amazon hardwood native species. Atoyebi et al. [9] observed values of loose bulk density between $1052\text{--}1639 \text{ kg/m}^3$ for particleboards made of wood sawdust, cement, and palm kernel shell (PKS), whereas Park et al. [48] obtained values between 876 kg/m^3 and 984 kg/m^3 for wood-lime boards. Comparing these results with the ones obtained in the present study, it is possible to observe that cement wood particleboards with banana pseudostem waste present higher values of bulk density.

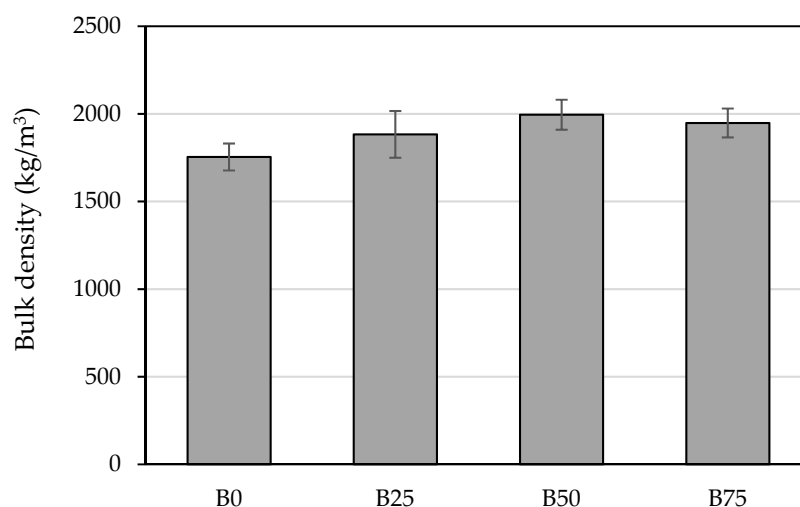


Figure 5. Average bulk density results.

Considering the strong dependence between thermal conductivity and bulk density obtained in previous studies [53–55], the results of thermal conductivity are in line with those obtained for bulk density. A higher density of CBPB induced fewer voids, thus leading to higher thermal conductivity [2]. Figure 6 shows the values of density plotted against the thermal conductivity (Figure 6a). The results are also in agreement with a naked-eye visualization of the samples' cut surface, which shows that the voids' prevalence decreased with the replacement of wood particles by banana tree waste, at least up to 50%; past that amount, visual differentiation was not possible.

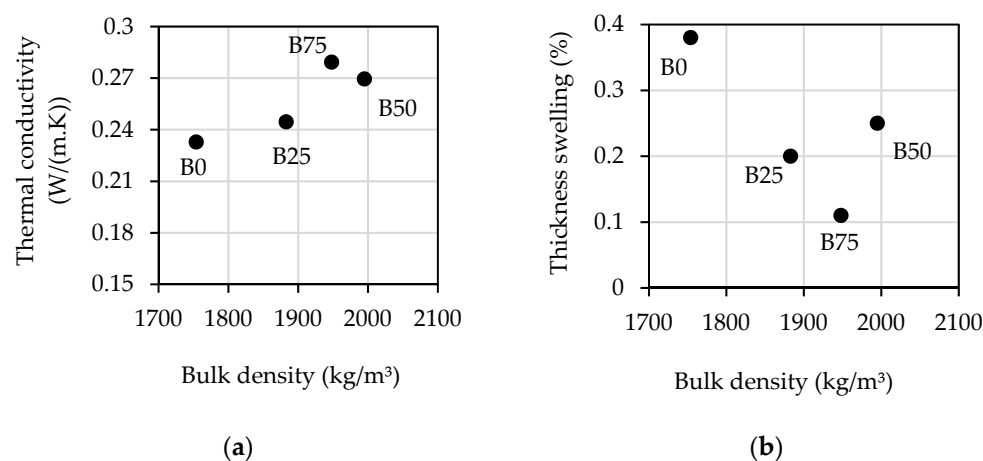


Figure 6. Comparison: (a) between bulk density and thermal conductivity; (b) between bulk density and thickness swelling.

3.3. Dimensional Stability

The thickness swelling was determined after 24 h of water immersion, and results are presented in Figure 6b and related to the bulk density. Specimens B0 (without banana pseudostem fibres in its composition) show the highest thickness swelling (0.38%). Thickness swelling seems to decrease with the substitution of wood particles by banana fibres (B25 at 0.20%; B50 at 0.25%) with the lowest thickness swelling recorded for B75 specimens (0.11%).

This thickness swelling decrease with the replacement of wood particles by banana fibres can be justified by either a larger volume of voids in the full wood CBPB with lower values of density and greater water absorption or the hygroscopicity of wood, which also needs to be considered, because the free OH groups of the cellulose contact with

water and form hydrogen bonds [2,56]. It seems that lower density is caused by a lower number of voids but also by improved bonding between cement, wood, and banana fibres, contributing to lower thickness swelling. Similar results were found by Cavdar et al. [26] by adding black sludge into CBPB composition instead of grey sludge and by Rocha Almeida et al. [24], who observed that lower density leads to higher thickness swelling due to a greater number of voids that allow water absorption.

He et al. [2] measured the thickness swelling of wood-cement boards with magnesium oxychloride in their composition and obtained values ranging between 0.11% and 0.44%, whereas Okino et al. [11] tested a mixture of eucalypt and rubberwood in CBPB composition and obtained higher values of thickness swelling, in the range 1.5–1.8%. Rocha Almeida et al. [24] reported values of thickness swelling between 0.15% and 0.27%. The result of thickness swelling obtained in the present study for specimens B0 is lower than those obtained by Okino et al. [11], slightly higher than those reported by Rocha Almeida et al. [24], but in the range of those obtained by He et al. [2].

3.4. Biological Susceptibility to Moulds

The results of the average rate of mould growth for sanded and unsanded CBPB surfaces are summarized in Table 4. No growth was detected during or at the end of the 4 week testing for unsanded surfaces. This can be due to the high alkalinity of the boards, with documented pH ranges between 11 and 13, which limits fungal colonization and development [5,12,46], and also by the fact that wood and/or banana fibres are not directly exposed to the fungi, being fully encapsulated by the cement paste.

Table 4. Average rate (\pm standard deviation) of mould growth (n = 3).

Specimens		Mould Development			
		Week 1	Week 2	Week 3	Week 4
Unsanded surface	B0u	0	0	0	0
	B25u	0	0	0	0
	B50u	0	0	0	0
	B75u	0	0	0	0
Sanded surface	B0p	0	0	0.33 \pm 0.58	0.33 \pm 0.58
	B25p	0	0	0.33 \pm 0.58	0.33 \pm 0.58
	B50p	0	0	0.33 \pm 0.58	0.67 \pm 0.58
	B75p	0	0.33 \pm 0.58	0.67 \pm 0.58	0.67 \pm 0.58
Viability control (maritime pine)	C (pw)	3.33 \pm 0.58	4	4	4

Scale: 0—no growth; 1—traces of growth; 2—light growth; 3—moderate growth; 4—heavy growth.

When considering the sanded surface specimens, the maximum rate of mould growth was obtained between the third and the fourth weeks of exposure, though only traces of growth (grade 1) were registered. Similar results were observed by Okino et al. [12], who only detected a slight presence of mycelium in the surface of CBPB composed of treated cypress particles. However, in the present study, the replacement of pine wood particles by banana fibres slightly increased the CBPB biological susceptibility (Table 4).

All the controls (maritime pine) were rated as 4 from the second week of testing (Table 4), which confirms the validity of the test.

4. Conclusions

In this study, the viability of producing cement-bonded particleboards (CBPB) with increasing replacement of pine wood particles with banana pseudostem waste fibres was assessed, opening a new option to manage this waste. Test specimens were produced assuming 0%, 25%, 50%, and 75% partial replacement of wood particles with banana pseudostem fibres. The bulk density, thermal conductivity, and dimensional stability of the

different specimens were assessed. The immediate (unsanded surfaces, reproducing new boards) and long-term (sanded surfaces, reproducing weathered ones) mould susceptibility of the boards was also investigated. The following conclusions can be drawn:

- The thermal conductivity of the CBPB increased with the replacement of wood by banana fibres and ranged between 0.233 W/(m.K) and 0.279 W/(m.K).
- The bulk density values, ranging between 1754–1995 kg/m³, were generally higher than those reported in the literature for other particleboards. Moreover, the bulk density generally increased with the proportion of banana fibre, being the highest value obtained for CBPB with an equal proportion of wood particles and banana fibres.
- Specimens with a higher percentage of banana fibres presented less thickness swelling and higher dimensional stability.
- Although cement-bonded particleboards with unsanded surfaces showed no signs of biological growth, the boards with sanded surfaces simulating some surface wear over time had increased bio-susceptibility. Under the conditions of the test performed, the biological susceptibility to the moulds *A. niger* and *P. funicullosum* of the boards slightly increased with the percentage of banana fibres.

The results demonstrate the viability of producing cement-bonded particleboards with partial replacement of raw pine wood fibres by a waste, namely banana pseudostem fibres. Further studies are necessary to optimize the composition of the boards, as well as to evaluate their mechanical properties. The production process can also be optimized, thus allowing the implementation of these innovative cement-bonded particleboards by the industry.

Author Contributions: Conceptualization, methodology, investigation, validation, writing–review and editing, L.N.; formal analysis, writing–original draft, visualization, E.C.; formal analysis, writing–original draft, visualization, methodology, investigation, J.L.P.; investigation, data curation, writing–review and editing, B.F.; resources, methodology, investigation, V.S.; conceptualization, methodology, investigation, validation, writing–review and editing, supervision, funding acquisition, project administration, P.F. All authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Portuguese Foundation for Science and Technology (FCT) with PhD grant PD/BD/150579/2020, as part of the Eco-Construction and Rehabilitation Programme (EcoCore).

Data Availability Statement: Data are available from the corresponding author upon request.

Acknowledgments: The authors are grateful to the CERIS research centre through the strategic project UIDB/04625/2020. The collaboration of VIROC, Investwood is also acknowledged.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Chen, L.; Wang, L.; Tsang, D.C.W.; Mechtcherine, V.; Poon, C.S. Efficacy of green alternatives and carbon dioxide curing in reactive magnesia cement-bonded particleboards. *J. Clean. Prod.* **2020**, *258*, 120997. [\[CrossRef\]](#)
2. He, P.; Hossain, M.U.; Poon, C.S.; Tsang, D.C.W. Mechanical, durability and environmental aspects of magnesium oxychloride cement boards incorporating waste wood. *J. Clean. Prod.* **2019**, *207*, 391–399. [\[CrossRef\]](#)
3. Ferrandez-Villena, M.; Ferrandez-Garcia, C.E.; Garcia-Ortuño, T.; Ferrandez-Garcia, A.; Ferrandez-Garcia, M.T. Properties of cement-bonded particleboards made from Canary Islands palm (*Phoenix canariensis* Ch.) trunks and different amounts of potato starch. *Forests* **2020**, *11*, 560. [\[CrossRef\]](#)
4. Rana, M.N.; Islam, M.N.; Nath, S.K.; Das, A.K.; Ashaduzzaman, M.; Shams, M.I. Influence of chemical additive on the physical and mechanical properties of cement-bonded composite panels made from jute stick. *J. Build. Eng.* **2020**, *31*, 101358. [\[CrossRef\]](#)
5. Farag, E.; Alshebani, M.; Elhrari, W.; Klash, A.; Shebani, A. Production of particleboard using olive stone waste for interior design. *J. Build. Eng.* **2020**, *29*, 101119. [\[CrossRef\]](#)
6. Adelusi, E.A.; Olaoye, K.O.; Adebawo, F.G. Strength and dimensional stability of cement-bonded boards manufactured from mixture of *Ceiba pentandra* and *Gmelina arborea* sawdust. *J. Eng. Res. Rep.* **2019**, *8*, 1–10. [\[CrossRef\]](#)
7. Dadile, A.M.; Sotannnde, O.A.; Alao, J.S. Physico-mechanical properties of cement-bonded particleboards made from date palm fibres (*Phoenix dactylifera*) and obeche sawdust (*Triplochyton schleroxylon*). *J. Mater. Sci. Res. Rev.* **2019**, *4*, 1–5.

8. Hossain, M.U.; Wang, L.; Yu, I.K.M.; Tsang, D.C.W.; Poon, C.S. Environmental and technical feasibility study of upcycling wood waste into cement-bonded particleboard. *Constr. Build. Mater.* **2018**, *173*, 474–480. [\[CrossRef\]](#)
9. Atoyebi, O.D.; Awolusi, T.F.; Davies, I.E.E. Artificial neural network evaluation of cement-bonded particle board produced from red iron wood (*Lophira alata*) sawdust and palm kernel shell residues. *Case Stud. Constr. Mater.* **2018**, *9*, e00185. [\[CrossRef\]](#)
10. Sousa, J.P. Cement Bonded Particle Board VIROC. Technical File. Available online: https://www.investwood.pt/wp-content/uploads/2020/10/VIROC_DTA_2020.1_EN.pdf (accessed on 29 July 2020).
11. Okino, E.Y.A.; de Sousa, M.R.; Santana, M.A.E.; da Alves, M.V.S.; de Sousa, M.E.; Teixeira, D.E. Cement-bonded wood particleboard with a mixture of eucalypt and rubberwood. *Cem. Concr. Compos.* **2004**, *26*, 729–734. [\[CrossRef\]](#)
12. Okino, E.Y.A.; de Sousa, M.R.; Santana, M.A.E.; da Alves, M.V.S.; de Sousa, M.E.; Teixeira, D.E. Physico-mechanical properties and decay resistance of Cupressus spp. cement-bonded particleboards. *Cem. Concr. Compos.* **2005**, *27*, 333–338. [\[CrossRef\]](#)
13. Quiroga, A.; Rintoul, I. Mechanical properties of hierarchically structured wood-cement composites. *Constr. Build. Mater.* **2015**, *84*, 253–260. [\[CrossRef\]](#)
14. Wang, L.; Chen, S.S.; Tsang, D.C.W.; Poon, C.-S.; Shih, K. Recycling contaminated wood into eco-friendly particleboard using green cement and carbon dioxide curing. *J. Clean. Prod.* **2016**, *137*, 861–870. [\[CrossRef\]](#)
15. Soroushian, P.; Aouadi, F.; Chowdhury, H.; Nossoni, A.; Sarwar, G. Cement-bonded straw board subjected to accelerated processing. *Cem. Concr. Compos.* **2004**, *26*, 797–802. [\[CrossRef\]](#)
16. Jorge, F.C.; Pereira, C.; Ferreira, J.M.F. Wood-cement composites: A review. *Eur. J. Wood Wood Prod.* **2004**, *62*, 370–377. [\[CrossRef\]](#)
17. Gaspar, F.; Bakatovich, A.; Davydenko, N.; Joshi, A. Building insulation materials based on agricultural wastes. In *Bio-Based Materials and Biotechnologies for Eco-Efficient Construction*; Elsevier: Amsterdam, The Netherlands, 2020; pp. 149–170. [\[CrossRef\]](#)
18. Liuzzi, S.; Sanarica, S.; Stefanizzi, P. Use of agro-wastes in building materials in the Mediterranean area: A review. *Energy Procedia* **2017**, *126*, 242–249. [\[CrossRef\]](#)
19. Madurwar, M.V.; Ralegaonkar, R.V.; Mandavgane, S.A. Application of agro-waste for sustainable construction materials: A review. *Constr. Build. Mater.* **2013**, *38*, 872–878. [\[CrossRef\]](#)
20. Maraveas, C. Production of sustainable construction materials using agro-wastes. *Materials* **2020**, *13*, 262. [\[CrossRef\]](#) [\[PubMed\]](#)
21. Viel, M.; Collet, F.; Lanos, C. Chemical and multi-physical characterization of agro-resources' by-product as a possible raw building material. *Ind. Crop. Prod.* **2018**, *120*, 214–237. [\[CrossRef\]](#)
22. Akinyemi, B.A.; Dai, C. Development of banana fibers and wood bottom ash modified cement mortars. *Constr. Build. Mater.* **2020**, *241*, 118041. [\[CrossRef\]](#)
23. Borysiuk, P.; Jencyk-Tolloczko, I.; Auriga, R.; Kordzikowski, M. Sugar beet pulp as raw material for particleboard production. *Ind. Crop. Prod.* **2019**, *141*, 111829. [\[CrossRef\]](#)
24. Rocha Almeida, R.; Del Menezzi, C.H.S.; Teixeira, D.E. Utilization of the coconut shell of babaçu (*Ornignya* sp.) to produce cement-bonded particleboard. *Bioresour. Technol.* **2002**, *85*, 159–163. [\[CrossRef\]](#)
25. Cabral, M.R.; Nakanishi, E.Y.; Mármol, G.; Palacios, J.; Godbout, S.; Lagacé, R.; Junior, H.S.; Fiorelli, J. Potential of Jerusalem Artichoke (*Helianthus tuberosus* L.) stalks to produce cement-bonded particleboards. *Ind. Crop. Prod.* **2018**, *122*, 214–222. [\[CrossRef\]](#)
26. Cavdar, A.D.; Yel, H.; Boran, S.; Pesman, E. Cement type composite panels manufactured using paper mill sludge as filler. *Constr. Build. Mater.* **2017**, *142*, 410–416. [\[CrossRef\]](#)
27. Nazerian, M.; Sadeghiipah, V. Cement-bonded particleboard with a mixture of wheat straw and poplar wood. *J. For. Res.* **2013**, *24*, 381–390. [\[CrossRef\]](#)
28. Omoniyi, T.E.; Olorunnisola, A.O. Effects of manufacturing techniques on the physico-mechanical properties of cement-bonded bagasse fiber composite. *J. Nat. Fibers* **2020**, 1–12. [\[CrossRef\]](#)
29. Ogunsile, B.O.; Adepegba, J.A. Cement bonded particle board from Musa paradisiaca stalk. *Pac. J. Sci. Technol.* **2015**, *16*, 12–20.
30. Nadhari, W.N.A.W.; Danish, M.; Nasir, M.S.R.M.N.; Geng, B.J. Mechanical properties and dimensional stability of particleboard fabricated from steam pre-treated banana trunk waste particles. *J. Build Eng.* **2019**, *26*, 100848. [\[CrossRef\]](#)
31. Israeli, Y.; Lahav, E. Banana. *Encycl. Appl. Plant Sci.* **2017**, pp. 363–381. [\[CrossRef\]](#)
32. FAO. *Medium-Term Outlook: Prospects for Global Production and Trade in Bananas and Tropical Fruits*; FAO: Rome, Italy, 2020; Available online: <http://www.fao.org/3/ca7568en/ca7568en.pdf> (accessed on 5 August 2020).
33. FAO (Food and Agriculture Organization of the United Nation). *Banana Market Review: Preliminary Results 2019*; FAO: Rome, Italy, 2020; Available online: <http://www.fao.org/3/ca9212en/ca9212en.pdf> (accessed on 5 August 2020).
34. Cordeiro, N.; Belgacem, M.N.; Torres, I.C.; Moura, J.C.V.P. Chemical composition and pulping of banana pseudo-stems. *Ind. Crop. Prod.* **2004**, *19*, 147–154. [\[CrossRef\]](#)
35. Sing Nee Nigam, P.; Pandey, A. *Biotechnology for Agro-Industrial Residues Utilization*. 2009. Available online: <http://link.springer.com/10.1007/978-1-4020-9942-7> (accessed on 5 August 2020).
36. Fernandes, B.; Silva, V.; Faria, P. Cement-wood boards with banana tree waste for buildings rehabilitation. In *Proceedings ENCORE2020—4º Encontro de Conservação e Reabilitação de Edifícios, 3–6 Novembro 2020*; Menezes, M., Veiga, M.R., Silva, A.S., Nunes, L., Machado, J.S., Eds.; LNEC: Lisboa, Portugal, 2020; pp. 663–672. (In Portuguese)
37. EN 1097-3. *Tests for Mechanical and Physical Properties of Aggregates—Part 3: Determination of Loose Bulk Density and Voids*; CEN: Brussels, Belgium, 1998.
38. Wang, L.; Chen, S.S.; Tsang, D.C.W.; Poon, C.S.; Shih, K. Value-added recycling of construction waste wood into noise and thermal insulating cement-bonded particleboards. *Constr. Build. Mater.* **2016**, *125*, 316–325. [\[CrossRef\]](#)

39. Wong, M.C.; Hendrikse, S.I.S.; Sherrell, P.C.; Ellis, A.V. Grapevine waste in sustainable hybrid particleboard production. *Waste Manag.* **2020**, *118*, 501–509. [[CrossRef](#)] [[PubMed](#)]
40. Nemli, G.; Demirel, S. Relationship Between the Density Profile and the Technological Properties of the Particleboard Composite. *J. Compos. Mater.* **2007**, *41*, 1793–1802. [[CrossRef](#)]
41. EN 323. Wood-based panels. In *Determination of Density*; CEN: Brussels, Belgium, 1993.
42. EN 12664. Thermal performance of building materials and products. Determination of thermal resistance by means of guarded hot plate and heat flow meter methods. In *Dry and Moist Products of Medium and Low Thermal Resistance*; CEN: Brussels, Belgium, 2001.
43. EN 317. Particleboards and fibreboards. In *Determination of Swelling in Thickness after Immersion in Water*; CEN: Brussels, Belgium, 1993.
44. ASTM D5590-17. *Determining the Resistance of Paint Films and Related Coatings to Fungal Defacement by Accelerated Four-Week Agar Plate Assay*; ASTM International: Pennsylvania, PA, USA, 2017.
45. ASTM C1338-19. *Standard Test Method for Determining Fungi Resistance of Insulation Materials and Facings*; ASTM International: Pennsylvania, PA, USA, 2019.
46. Parracha, J.L.; Borsoi, G.; Flores-Colen, I.; Veiga, R.; Nunes, L.; Dionísio, A.; Gomes, M.G.; Faria, P. Performance parameters of ETICS: Correlating water resistance, bio-susceptibility and surface properties. *Constr. Build. Mater.* **2021**, *272*, 121956. [[CrossRef](#)]
47. Davies, I.O.E.; Davies, O.O.A. Agro-waste-cement particleboards: A review. *MAYFEB J. Environ. Sci.* **2017**, *2*, 10–26.
48. Park, J.H.; Kang, Y.; Lee, J.; Chang, S.J.; Wi, S.; Kim, S. Development of wood-lime boards as building materials improving thermal and moisture performance based on hygrothermal behavior evaluation. *Constr. Build. Mater.* **2019**, *204*, 576–585. [[CrossRef](#)]
49. Wang, C.G.; Zhang, S.G.; Wu, H. Performance of Cement Bonded Particleboards Made from Grapevine. *Adv. Mater. Res.* **2013**, *631–632*, 765–770. [[CrossRef](#)]
50. LNEC. Maritime pine for structures. In *Madeira para Construção n° M2*, 2nd ed.; LNEC: Lisboa, Portugal, 2014; p. 12. (In Portuguese)
51. Idicula, M.; Boudenne, A.; Umadevi, L.; Ibos, L.; Candau, Y.; Thomas, S. Thermophysical properties of natural fibre reinforced polyester composite. *Compos. Sci. Technol.* **2006**, *66*, 2719–2725. [[CrossRef](#)]
52. Macêdo, A.N.; Costa e Souza, A.A.; Neto, B.B.P. Cement-wood particleboards made with waste from the Amazon timber industry. *Ambiente Construído* **2012**, *12*, 131–150. (In Portuguese) [[CrossRef](#)]
53. Chikhi, M.; Agoudjil, B.; Boudenne, A.; Gherabli, A. Experimental investigation of new biocomposite with low cost for thermal insulation. *Energy Build* **2013**, *66*, 267–273. [[CrossRef](#)]
54. Collet, F.; Pretot, S. Thermal conductivity of hemp concretes: Variation with formulation, density and water content. *Constr. Build. Mater* **2014**, *65*, 612–619. [[CrossRef](#)]
55. Nguyen, D.M.; Grillet, A.-C.; Diep, T.M.H.; Bui, Q.B.; Woloszyn, M. Influence of thermo-pressing conditions on insulation materials from bamboo fibers and proteins based bone glue. *Ind. Crop. Prod.* **2018**, *111*, 834–845. [[CrossRef](#)]
56. Bledzki, A.K.; Reihmane, S.; Gassan, J. Thermoplastics reinforced with wood fillers: A literature review. *Polym. Plast. Technol. Eng.* **1998**, *37*, 451–468. [[CrossRef](#)]