

Abstract

# Magnetized Dextrin: Eco-Friendly Effective Nanocatalyst for the Synthesis of Dihydropyrano[2,3-c]pyrazole Derivatives †

Zeinab Amiri-Khamakani, Fereshte Hassanzadeh-Afruzi and Ali Maleki \*

Catalysts and Organic Synthesis Research Laboratory, Department of Chemistry, Iran University of Science and Technology, Tehran 16846-13114, Iran; zeinabamiri74@yahoo.com (Z.A.-K.); hassanzadeh\_f@chem.iust.ac.ir (F.H.-A.)

\* Correspondence: maleki@iust.ac.ir

† Presented at the 24th International Electronic Conference on Synthetic Organic Chemistry, 15 November–15 December 2020; Available online: <https://ecsoc-24.sciforum.net/>.

**Abstract:** Dextrin is a water soluble polysaccharide obtained by hydrolysis of starch and glycogen. This low molecular weight biopolymer with valuable properties such as biodegradability, biocompatibility, good availability, and high reactivity can be an appropriate substance to fabricate the environmentally friendly catalysts. The magnetized dextrin was prepared via facile co-precipitation procedure of iron salts in the presences of dextrin under alkaline condition. Then, it was characterized by different conventional analyses. Eventually, the catalytic application of obtained nanocomposite was evaluated for the synthesis dihydropyrano[2,3-c]pyrazole derivatives through multi-component reaction of hydrazine hydrate, ethyl acetoacetate, aromatic aldehydes, and malononitrile. Biocompatible nanocatalyst, simple procedure, short reaction times, and catalyst reusability after four consecutive runs with negligible decrease in catalytic efficiency are some merits of the presented method.

**Keywords:** Dextrin; eco-friendly catalyst; multicomponent reaction; pyranopyrazole

**Citation:** Amiri-Khamakani, Z.; Hassanzadeh-Afruzi, F.; Maleki, A. Magnetized Dextrin: Eco-Friendly Effective Nanocatalyst for the Synthesis of Dihydropyrano[2,3-c]pyrazole Derivatives. *Chem. Proc.* **2021**, *3*, 101. <https://doi.org/10.3390/ecsoc-24-08285>

Academic Editors: Julio A. Seijas and M. Pilar Vázquez-Tato

Published: 14 November 2020

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Copyright:** © 2020 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<http://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

One of the important achievements of the principles of green chemistry is the design and fabrication of biocompatible catalysts [1]. Dextrin is a low molecular weight polysaccharide with chemical formula  $(C_6H_{10}O_5)_n$  which is obtained from the hydrolysis of starch or glycogen. Dextrin is composed of D-glucose units linked by  $\alpha$ -(1 → 4) or  $\alpha$ -(1 → 6) glycosides bonds (Figure 1) [2]. As a natural polymer, dextrin has outstanding properties for instance have great number of hydroxyl groups, water solubility, biodegradability, good stability, low cost, and non-toxicity. Therefore, it has been used in environmental chemistry, biochemistry, pharmaceutical chemistry, and more recently in catalysts [3].

The presence of a large number of reactive functional groups in its chemical structure provided chemical modification to fabricate the diverse compounds and with catalytic potential application. In this work, a composite consisting of dextrin and  $Fe_3O_4$  MNPs prepared via simple procedure. This composite has the advantages of dextrin for instance the presence of large number of hydroxyl groups that can form a hydrogen bond with the starting reactants and accelerate the reaction as well as the advantages of  $Fe_3O_4$  MNPs such as high surface area, Lewis acid sites, and the possibility of recovery and reusability. Multicomponent reactions (MCRs) are one of the most important approach to construct the organic compounds which offer outstanding benefits such as high atomic efficiency, time and energy saving, and environmental friendliness [3,4]. Dihydropyrano [2,3-c]pyrazole is a heterocyclic compound with potential application in medicinal and pharmaceutical chemistry and significant role as building blocks in the preparation of valuable drugs for

instance antimicrobial, antiviral, analgesic, anti-inflammatory, anticancer, and anti-proliferative [5]. In continues to our research on MCRs and nanomaterials [6–8], in present work, magnetized dextrin was used as a hybrid nanocatalyst in the synthesis of dihydropyrano[2,3-c]pyrazoles derivatives, via one-pot condensation of ethyl acetoacetate, hydrazine hydrate, malononitrile, and aromatic aldehydes (Scheme 1).


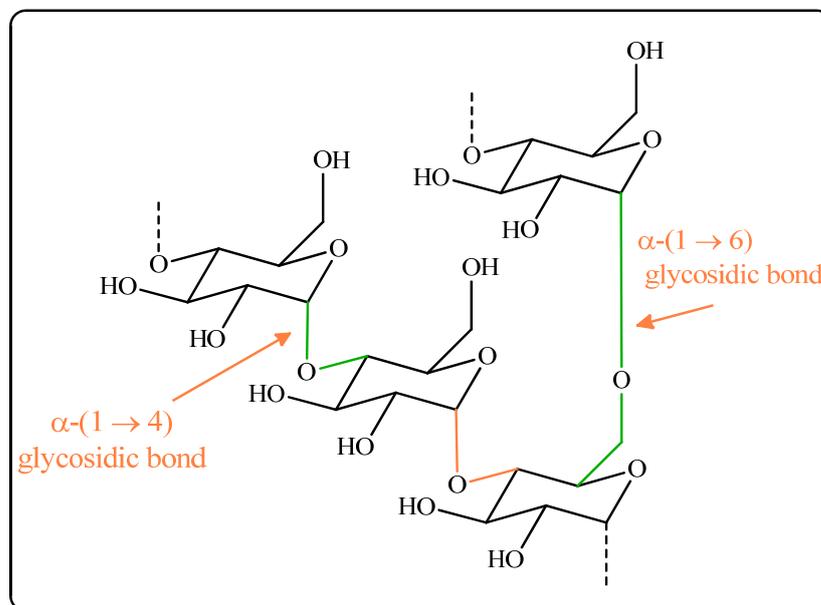


Figure 1. Chemical structure of dextrin.

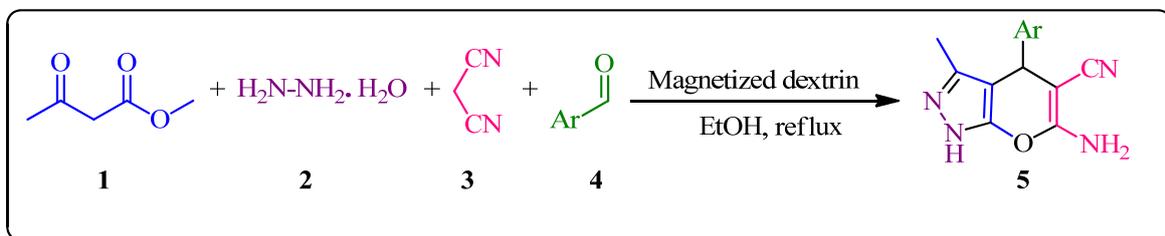

Scheme 1. Synthesis of dihydropyrano[2,3-c]pyrazoles derivatives.

## 2. Experimental

### 2.1. General

All chemicals were purchased from Merck and Aldrich companies. The melting points of the prepared derivatives were measured by an electrothermal 9100 apparatus. Elemental analysis of the nanocatalyst was carried out by energy-dispersive X-ray (EDX) analysis recorded on Numerix JEOL-JDX. Fourier transform infrared (FT-IR) spectra were recorded on a Shimadzu 8400 S spectrometer using KBr pellets. X-ray diffraction (XRD) pattern of the nanocatalyst was recorded on an X-ray diffractometer (Bruker D8 Advance) and the morphology of prepared nanocatalyst was studied by SEM using VEGA2 TESCAN instrument.

### 2.2. Preparation of Magnetized Dextrin Nanocomposite

First, 2 mmol  $\text{FeCl}_3 \cdot 6\text{H}_2\text{O}$  and 1 mmol  $\text{FeCl}_2 \cdot 4\text{H}_2\text{O}$  were dissolved in 100 mL of distilled water, then the aqueous solution of 0.35 g dextrin in 25 mL distilled was added to the solution. The temperature of the resulting mixture was raised to 90 °C and stirred under a nitrogen atmosphere for 1 h. Later,  $\text{NH}_4\text{OH}$  (25%) was added dropwise over 15 min to the stirring above suspension. The reaction continued for about one hour. Finally,

the black crude precipitate was collected by magnet, washed several times with distilled water and ethanol to remove non-reactive materials, and then dried at room temperature for 24 h to obtain magnetized dextrin nanocomposite.


### 2.3. General Procedure for the Synthesis of Dihydropyrano[2,3-*c*]pyrazole Derivatives

The mixture of hydrazine hydrate (2 mmol), ethyl acetoacetate (2 mmol), malononitrile (1 mmol), and aromatic aldehydes (1 mmol) were mixed together in the presence of 0.015 g of magnetized dextrin in ethanol and refluxed for appropriate time. The reaction progress was monitored by thin layer chromatography (TLC). Finally, after completion of the reaction, the catalyst was separated from the reaction mixture by an external magnet and high pure product was obtained by recrystallization of the crude precipitate in ethanol.

## 3. Results and Discussion

### 3.1. Characterization Magnetized Dextrin

Elemental analysis was employed to investigate the chemical composition of the magnetized dextrin. As can be seen in the Figure 2, the presence of C, O and Fe elements in the prepared nanocatalyst was confirmed by this analysis.

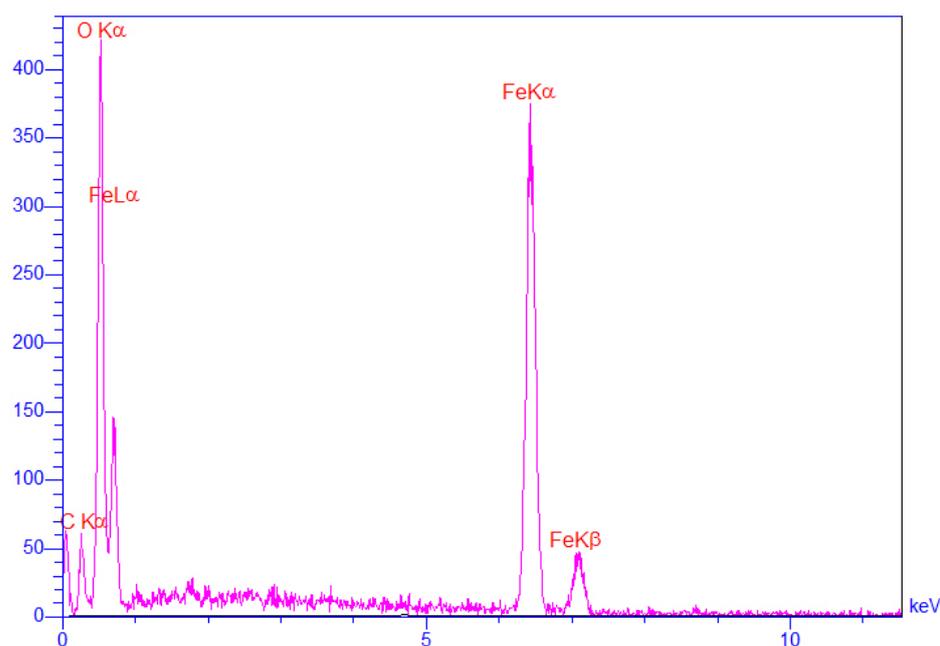

**Figure 2.** EDX analysis of magnetized dextrin nanocatalyst.

FT-IR spectra of magnetized dextrin (b) in comparison with dextrin (a) are observed in Figure 3. In the IR spectrum of dextrin, a broad absorption band at  $3438\text{ cm}^{-1}$  is related to the stretching vibration of O–H bond which is abundant in dextrin structure, adsorption band at  $2923\text{ cm}^{-1}$  is related to the stretching vibration of C–H bond, and the adsorption band at  $1153\text{ cm}^{-1}$  is attributed to the asymmetric vibration of the glycosidic C–O–C bond. Comparison of FT-IR spectra of magnetized dextrin and dextrin showed that in the magnetic dextrin spectrum, in addition to observing the main adsorptions of dextrin, two new absorptions at  $632$  and  $579\text{ cm}^{-1}$  appeared which is ascribed to the stretching vibrations of Fe–O bond of  $\text{Fe}_3\text{O}_4$  MNPs [3].

The SEM image was used to show the morphology and particle size of the prepared nanocatalysts. As is shown in Figure 4, there are aggregation of spherical like particles which ascribed to  $\text{Fe}_3\text{O}_4$  MNPs, present on the surface of dextrin. The average particle size of a magnetized dextrin is about 85 nm.

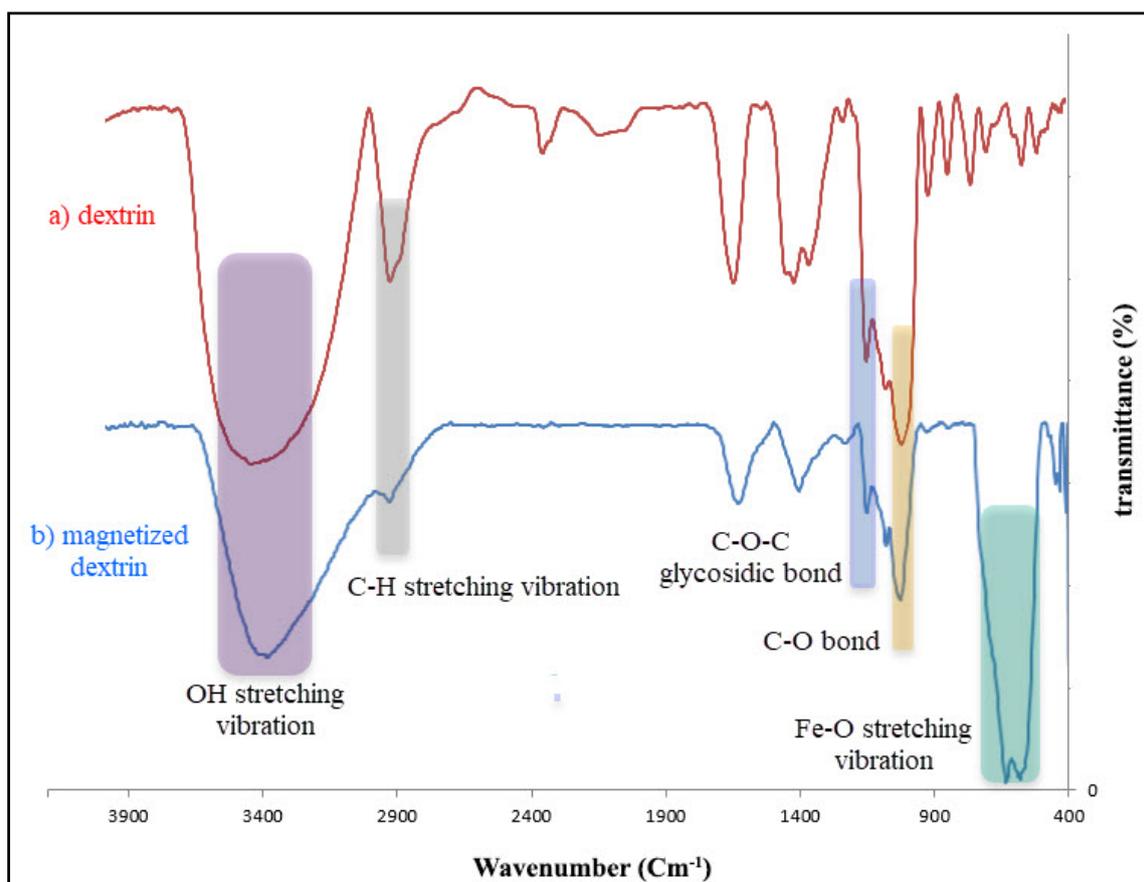


Figure 3. FTIR spectra of dextrin and the magnetized dextrin nanocatalyst.


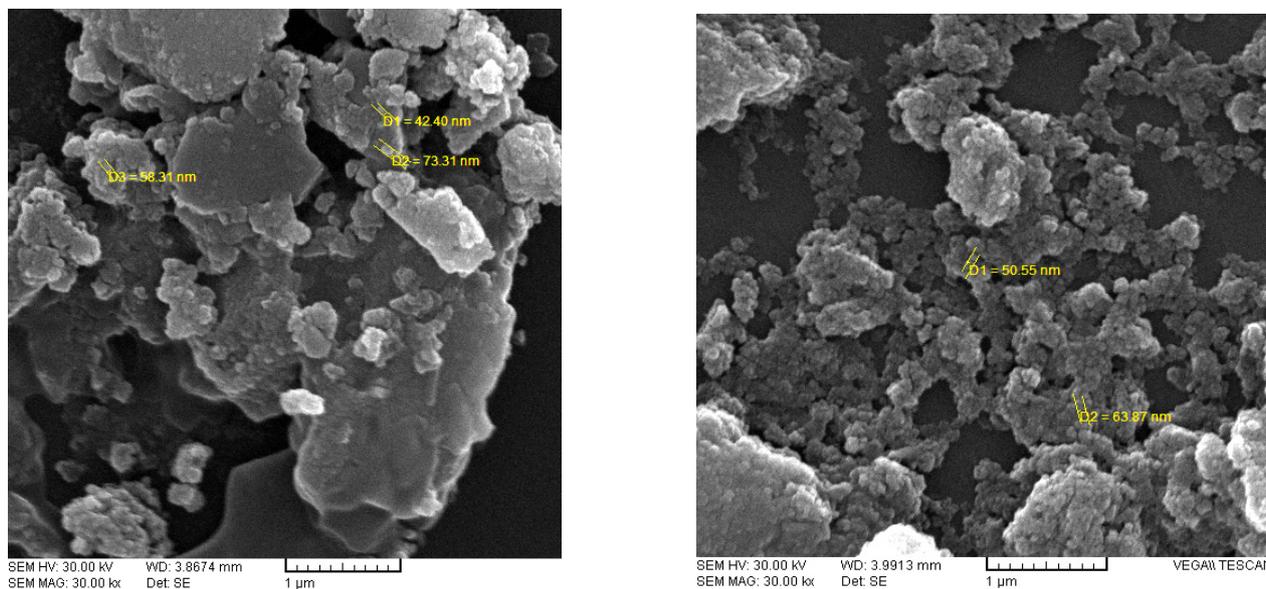


Figure 4. SEM images of the magnetic dextrin nanocatalyst.

XRD analysis was used to study the crystalline structure of prepared nanocatalyst. As reported in the literature, XRD pattern of dextrin has two broad peaks signifying its amorphous nature [9]. The XRD patterns of magnetized dextrin and standard  $\text{Fe}_3\text{O}_4$  MNPs were compared in Figure 5. The synthesized nanocomposite exhibited several peaks at  $2\theta$

= 17.5°, 30.1°, 35.5°, 37.9°, 57.4°, and 69.7° that are in accordance with the standard pattern of Fe<sub>3</sub>O<sub>4</sub> MNPs with card no. JCPDS, 00-001-111.

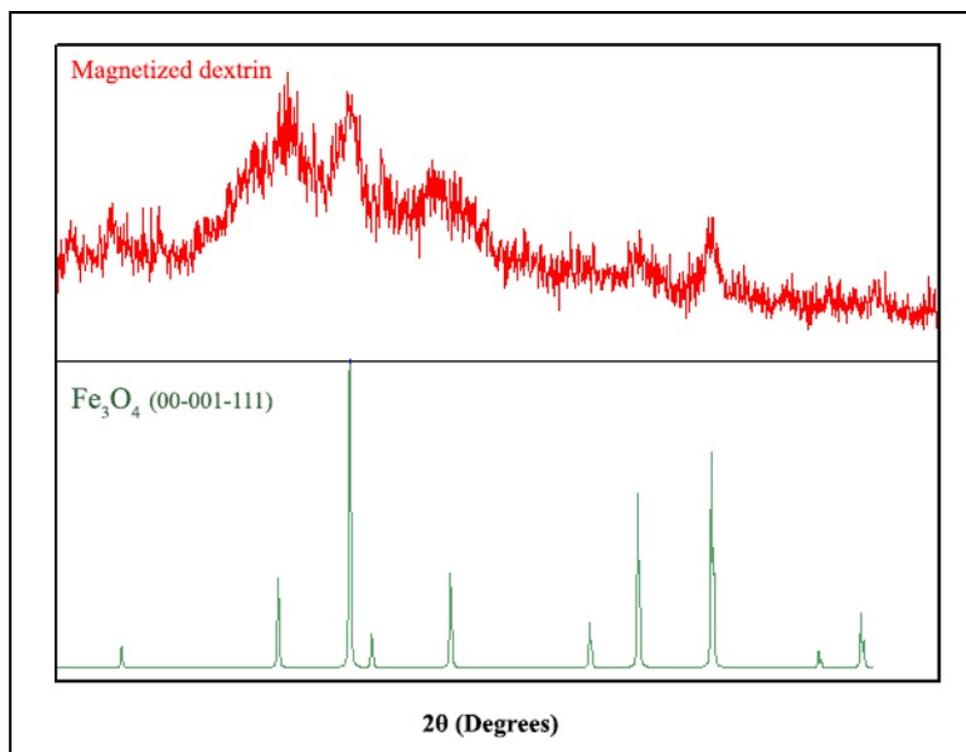

**Figure 5.** XRD pattern of the magnetized dextrin nanocatalyst and standard Fe<sub>3</sub>O<sub>4</sub>.

### 3.2. Catalytic Application of the Magnetized Dextrin in the Synthesis of Dihydropyrano[2,3-*c*]pyrazole Derivatives

The synthesis of dihydropyrano[2,3-*c*]pyrazole derivatives using some aromatic aldehydes in optimum condition was studied and in order to evaluate generality, and limitation of this protocol. As is observed in Table 1, all examined aromatic aldehydes with electron withdrawing and electron donating substitution produced the satisfying corresponding products.

**Table 1.** Synthesis of dihydropyrano[2,3-*c*]pyrazole using the magnetized dextrin nanocatalyst

Entry	R	Product	Yield <sup>a</sup> (%)	Mp (°C)
1	4-Cl	4a	92	232–235 [5]
2	3-NO <sub>2</sub>	4b	90	236–239 [5]
3	4-OMe	4c	85	212–214 [5]
4	3-OMe	4d	89	245 [10]
5	4-Me	4e	84	193–195 [10]

<sup>a</sup> Isolated yield.

## 4. Conclusions

Magnetized dextrin nanocomposite was synthesized using as a green, retrievable, and cost-effective catalyst for synthesis of biologically active dihydropyrano[2,3-*c*]pyrazole derivatives. This procedure has advantages such as high efficiency products, mild reaction conditions, and easy separation of the product from the reaction mixture.

**Funding:** This research received no external funding.

**Institutional Review Board Statement:** Not applicable.

**Informed Consent Statement:** Not applicable.

**Data Availability Statement:** The data presented in this study are available on request from the corresponding author.

**Acknowledgments:** The authors gratefully acknowledge the partial support from the Research Council of the Iran University of Science and Technology.

## References

1. Baran, T.; Baran, N.Y.; Menteş, A. An easily recoverable and highly reproducible agar-supported palladium catalyst for Suzuki-Miyaura coupling reactions and reduction of o-nitroaniline. *Int. J. Biol. Macromol.* **2018**, *115*, 249–256.
2. Zare, E.N.; Lakouraj, M.M.; Kasirian, N. Development of effective nano-biosorbent based on poly m-phenylenediamine grafted dextrin for removal of Pb (II) and methylene blue from water. *Carbohydr. Polym.* **2018**, *201*, 539–548.
3. Maleki, A.; Hassanzadeh-Afrouzi, F.; Varzi, Z.; Esmaeili, M.S. Magnetic dextrin nanobiomaterial: An organic-inorganic hybrid catalyst for the synthesis of biologically active polyhydroquinoline derivatives by asymmetric Hantzsch reaction. *Mater. Sci. Eng. C* **2020**, *109*, 110502.
4. Maleki, A.; Varzi, Z.; Hassanzadeh-Afrouzi, F. Preparation and characterization of an eco-friendly ZnFe<sub>2</sub>O<sub>4</sub>@ alginate nano-composite catalyst and its application in the synthesis of 2-amino-3-cyano-4H-pyran derivatives. *Polyhedron* **2019**, *171*, 193–202.
5. Hajizadeh, Z.; Maleki, A. Poly (ethylene imine)-modified magnetic halloysite nanotubes: A novel, efficient and recyclable catalyst for the synthesis of dihydropyrano [2,3-c] pyrazole derivatives. *Mol. Catal.* **2018**, *460*, 87–93.
6. Maleki, A.; Firouzi-Haji, R.; Hajizadeh, Z. Magnetic guanidinylated chitosan nanobiocomposite: A green catalyst for the synthesis of 1, 4-dihydropyridines. *Int. J. Biol. Macromol.* **2018**, *116*, 320–326.
7. Maleki, A.; Jafari, A.A.; Yousefi, S. Green cellulose-based nanocomposite catalyst: Design and facile performance in aqueous synthesis of pyranopyrimidines and pyrazolopyranopyrimidines. *Carbohydr. Polym.* **2017**, *175*, 409–416.
8. Bahrami, S.; Hassanzadeh-Afrouzi, F.; Maleki, A. Synthesis and characterization of a novel and green rod-like magnetic ZnS/CuFe<sub>2</sub>O<sub>4</sub>/agar organometallic hybrid catalyst for the synthesis of biologically-active 2-amino-tetrahydro-4H-chromene-3-carbonitrile derivatives. *Appl. Organomet. Chem.* **2020**, *34*, e5949.
9. Zare, E.N.; Lakouraj, M.M. Biodegradable polyaniline/dextrin conductive nanocomposites: Synthesis, characterization, and study of antioxidant activity and sorption of heavy metal ions. *Iran. Polym. J.* **2014**, *23*, 257–266.
10. Eivazzadeh-Keihan, R.; Taheri-Ledari, R.; Khosropour, N.; Dalvand, S.; Maleki, A.; Mousavi-Khoshdel, S.M.; Sohrabi, H. Fe<sub>3</sub>O<sub>4</sub>/GO@ melamine-ZnO nanocomposite: A promising versatile tool for organic catalysis and electrical capacitance. *Colloids Surf. A Physicochem. Eng. Asp.* **2020**, *587*, 124335.