

Synthesis of CuO Quadrilateral Nanoplate Thin Films by Controlled Crystal Growth in a Two-Dimensional Microspace [†]

Mitsunori Yada * and Yuko Inoue

Faculty of Science and Engineering, Department of Chemistry and Applied Chemistry, Saga University, 1 Honjo, Saga 840-8502, Japan

* Correspondence: yada@cc.saga-u.ac.jp

[†] Presented at the 4th International Electronic Conference on Applied Sciences, 27 October–10 November 2023;Available online: <https://asec2023.sciforum.net/>.

Abstract: Thin films consisting of quadrilateral nanoplates of CuO on the surface of a Cu plate were successfully synthesized in a two-dimensional microspace by the hydrothermal oxidation of a Cu plate using aqueous (NH₄)₂S₂O₈ solution as the oxidizer. Selective crystal growth was clearly observed in the two-dimensional microspace formed between the Al₂O₃ and the Cu plates, and a highly crystalline CuO quadrilateral nanoplate thin film was formed on the surface of the Cu plate that faced the Al₂O₃ plate. Similar experiments were performed by replacing the Al₂O₃ plate with Cu, Ti, or SUS316L plates as the substrate, to investigate the effect of the substrate facing the Cu plate. Using different substrates resulted in significant differences in the morphology of the CuO thin film on the Cu plate facing the substrate. The present study demonstrates that the use of a two-dimensional microspace can be extremely effective in controlling the nanostructure of thin films.

Keywords: CuO; thin film; crystal growth; two-dimensional microspace

1. Introduction

Recently, cupric oxide (CuO) has been actively researched for use in a number of applications, in sensor materials [1], catalyst materials [2], lithium-ion secondary batteries [3], optoelectronic materials [4], pseudocapacitor electrode materials [5], and superhydrophobic materials [6], as well as for As(III) removal [7], hydrogen production [8], and photocatalytic water splitting [9]. Previous studies have shown that the properties of CuO are greatly influenced by its nanoscale morphology and the exposed crystallographic faces on its surface. Hence, to optimize the properties of CuO nanoparticles, it is important to avoid random aggregation and fabricate thin films wherein the morphology, arrangement, and aggregation of the nanoparticles are precisely controlled. Syntheses and applications of precisely controlled nanostructured CuO thin films have been reported by several groups [3,5,8,9]. The synthesis of ceramic nanoparticle thin films on metals (i.e., nanostructured ceramic thin film/metal composites) has become an active research area because these composites are extremely promising functional materials that combine the excellent mechanical properties and conductivity of the metal with the specific physical and chemical properties of the ceramic nanoparticles. Nanostructured CuO thin film/Cu composites have been synthesized by aqueous solution techniques [10–15] and thermal oxidation processes [16–22]. There are several reports on the uses of nanostructured CuO thin film/Cu composites as electrochemical sensors for detecting H₂O₂ [13], glucose [13], and H₂S [21]; field emission materials [18,20]; antimicrobial materials [15]; and cathodes in dye-sensitized solar cells [10].

Nanoparticles with specific morphology and structure can be synthesized using micro-reactors [23,24], where a tube with a micrometer-sized diameter is used as the one-dimensional reactor. The effective control of crystal growth in microspace has been reported; however, this method cannot be used to synthesize thin films. In the present



Citation: Yada, M.; Inoue, Y. Synthesis of CuO Quadrilateral Nanoplate Thin Films by Controlled Crystal Growth in a Two-Dimensional Microspace. *Eng. Proc.* **2023**, *56*, 173. <https://doi.org/10.3390/ASEC2023-15364>

Academic Editor: Elisabeta Szerb

Published: 26 October 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

study, we developed a novel method that uses a two-dimensional space with micrometer thickness and centimeter-scale length and width (i.e., a two-dimensional microspace) for the synthesis of nanostructured ceramic thin films. This method allows controlling the structures of ceramic thin films on the nanoscale by confining the reaction in the microspace. It is expected that using this method, new nanostructured ceramic thin film/metal composites with previously unreported nanostructures and morphologies with unique chemical and physical properties can be formed due to the effect of the two-dimensional microspace reaction. In particular, the present work is focused on the attempt to synthesize a nanostructured cupric oxide thin film on the surface of a copper plate by hydrothermal reaction in a two-dimensional microspace, using an aqueous solution of $(\text{NH}_4)_2\text{S}_2\text{O}_8$ as the oxidizer. This reaction yielded CuO quadrilateral nanoplate thin film/Cu composites, the unique structure of which could be attributed to the controlled crystal growth in the two-dimensional microspace. The effect of the substrates used for creating the two-dimensional microspace was also examined with respect to the crystal structure and nanomorphology of the CuO thin films.

2. Methods

A two-dimensional microspace was formed on a Cu plate ($20 \times 20 \times 0.3$ mm) by constructing a reaction field, as shown in Figure 1. A SUS316 wire with a 200 μm external diameter was wound over an Al_2O_3 plate ($20 \times 20 \times 1$ mm). The Al_2O_3 plate and the Cu plate were arranged to face each other and fixed using the SUS316 wire. Fixing these two plates created a 200 μm gap (i.e., a two-dimensional microspace). The fixed plates were soaked in a mixture of 1 mol/l $(\text{NH}_4)_2\text{S}_2\text{O}_8$ (2 mL), 10 mol/l NaOH (4 mL), and distilled water (9 mL), and allowed to react hydrothermally at 120 $^\circ\text{C}$ for 20 h. After the reaction, the Cu plate was repeatedly washed with distilled water and characterized. In the characterization experiments, the surface of the Cu plate that faced the Al_2O_3 plate was designated as surface A, while the surface of the Cu plate that faced away from the Al_2O_3 plate was designated as surface B. A similar reaction was carried out without using the Al_2O_3 plate, i.e., only the Cu plate was used. The surface of this Cu plate was designated as surface C. The effect of the composition of the substrate (that faced the Cu plate) on the crystal structure and morphology of the thin film was examined using a Cu plate, a SUS316L plate, or a Ti plate, respectively, instead of the Al_2O_3 plate, for the hydrothermal synthesis experiment. A Hitachi S-3000N microscope was used to acquire scanning electron microscopy (SEM) images. A Shimadzu XRD-6100 instrument with $\text{CuK}\alpha$ radiation was used to obtain X-ray diffraction (XRD) patterns.

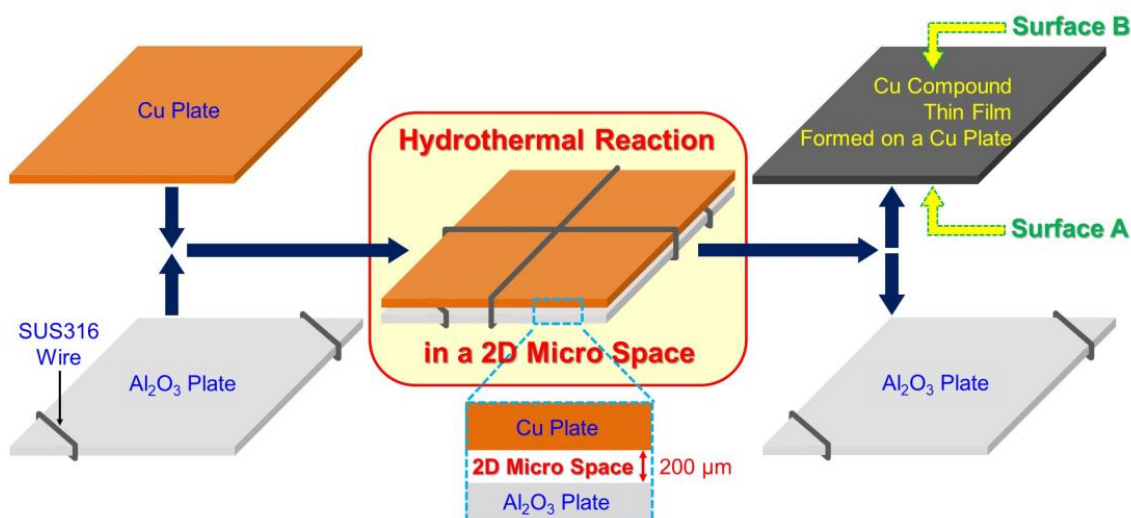


Figure 1. Schematic representation of the formation of a two-dimensional microspace.

3. Results and Discussion

The surface of the raw Cu plate was all smooth. Figure 2 shows the results obtained using the Al_2O_3 plate as the substrate. As shown in Figure 2a,b, a black thin film composed of quadrilateral nanoplates with side dimensions of approximately 0.6–2.3 μm (an average side dimension of 1.43 μm) and an average thickness of ca. 160 nm was synthesized on surface A. In contrast, surface B was coated by a thin film composed of lamellar structures with sizes of approximately 1 μm or less, with uneven edges and irregular shapes (Figure 2c,d). The SEM images of the surface C (Figure 2e,f) were similar to those of surface B. The XRD pattern of surface A (Figure 3a) showed nine sharp diffraction peaks attributed to monoclinic CuO, along with diffraction peaks from the Cu substrate. Two diffraction peaks attributed to Cu_2O were also observed, although their intensities were extremely low. Therefore, it was concluded that the principal crystallographic phase of the nanoplate thin film was CuO. Liu et al. [12] studied the reaction between Cu and $(\text{NH}_4)_2\text{S}_2\text{O}_8$ aqueous solution in the presence of NaOH, and reported the following scheme of reactions:

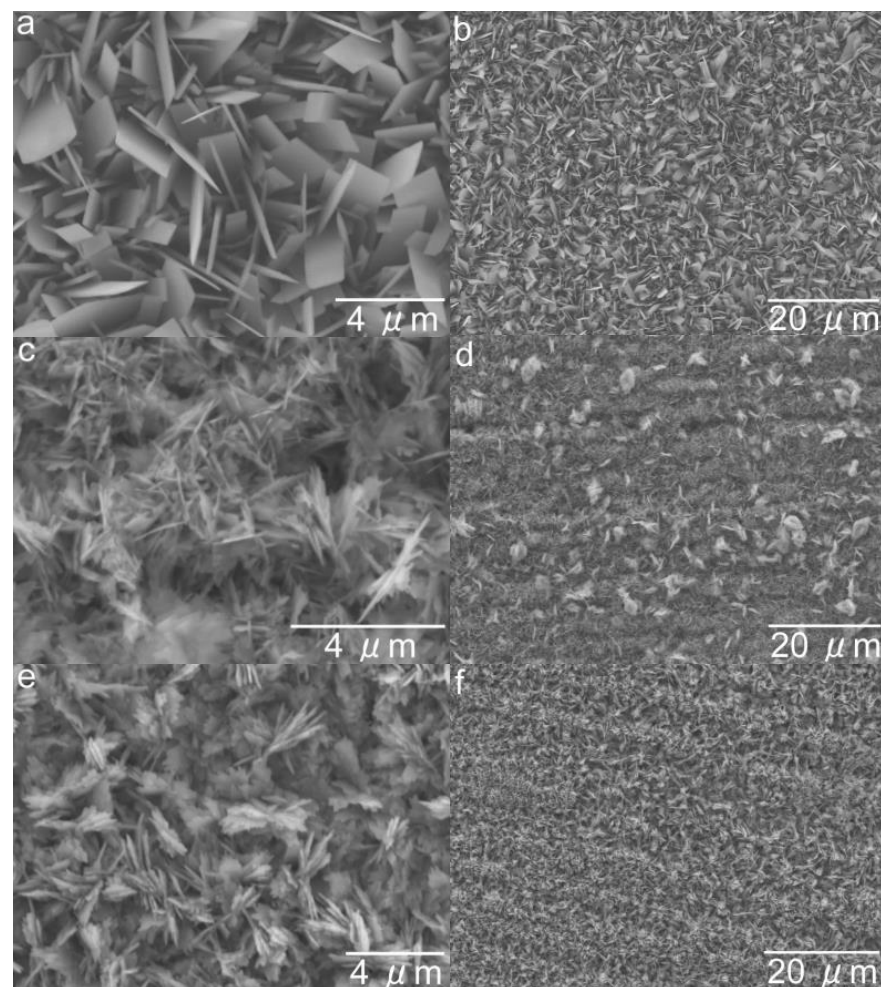



Figure 2. SEM images of thin films formed on the surfaces of the Cu plate obtained using an Al_2O_3 plate as the substrate; (a,b): surface A; (c,d): surface B; and (e,f): surface C.

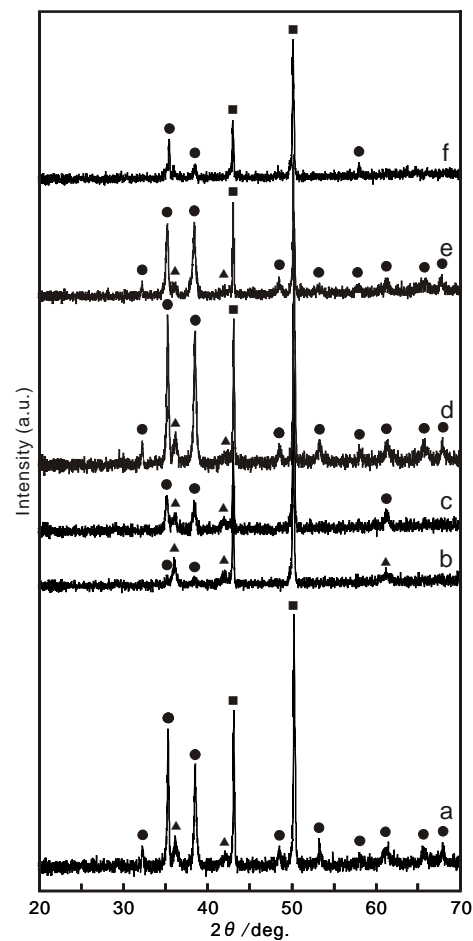


Figure 3. XRD patterns of thin films formed on the surfaces of Cu substrates obtained using (a–c) Al_2O_3 , (d) Cu, (e) SUS316L, and (f) Ti plates as the substrate; (a,d–f), surface A; (b), surface B; and (c) surface C. Peak assignment: ●: CuO; ■: Cu; ▲: Cu_2O .

In the present study, ions such as $[\text{Cu}(\text{OH})_4]^{2-}$ generated near the surface of the Cu plate were deposited onto surface A of the Cu plate as CuO quadrilateral nanoplates that form the CuO thin film. The XRD patterns of the thin films synthesized on surfaces B and C (Figure 3b,c) showed diffraction peaks attributed to CuO, but only a few peaks were observed and their intensities were markedly lower than those observed on surface A. On surface B, the intensities of the CuO peaks were lower than the intensities of the peaks from Cu_2O . On surface C, the intensities of the diffraction peaks attributed to CuO were slightly higher than those from Cu_2O . Therefore, it is obvious that a selective crystal growth of CuO occurred in the two-dimensional microspace formed between the Al_2O_3 plate and the Cu plate, and a highly crystalline CuO quadrilateral nanoplate thin film, which has not been reported previously, was synthesized. In the past, in the syntheses of nanostructured ceramic thin films, structure control at the nanoscale was achieved by controlling the composition, the concentrations of the precursor solutions, and the reaction temperature, or by using structure-directing agents such as surfactants. The present study revealed that a two-dimensional microspace can be extremely effective for the controlled synthesis of nanostructured materials. The possible sequence of events in this process of crystal growth in two-dimensional microspace can be described as follows: (1) the two-dimensional microspace moderately inhibited the diffusion of the raw material, and the generation and diffusion of CuO precursor ions near the Cu plate surface, (2) the rates of nucleation and crystal growth decreased, and (3) quadrilateral nanoplates with uniform sizes and shapes were selectively synthesized. Zou et al. [25] reported the formation of well-aligned arrays of monoclinic CuO nanoplatelets on the walls of a Teflon container, but

the corresponding SEM images were significantly different from those observed in our case. It was explained that this particular morphology was the result of a preferred orientation of the nanoplatelets along the [010] direction. Moura et al. [26] reported aggregates of monoclinic CuO plates with quadrilateral shapes and elucidated that CuO crystals grow preferentially along the [100] and [010] directions to form plates. Taking into account the two reports, we suppose that in our study, CuO crystals grew from the Cu substrate along the [010] direction vertically aligned with the Cu substrate and in the [100] direction when aligned parallel to the Cu substrate. On surfaces B and C, in the absence of a two-dimensional microspace, the diffusion of the raw material, and the generation and diffusion of CuO precursor ions near the Cu plate surface, readily occurred. Consequently, the rate of nucleation and crystal growth increased, resulting in the synthesis of thin films composed of poorly crystallized CuO and Cu₂O nanoparticles with different shapes with a two-dimensional morphology.

Similar experiments were conducted by substituting the Al₂O₃ plate with a Cu, Ti, or SUS316L plate as the substrate, to investigate the effect of the nature of the substrate facing the Cu plate. All these substrates showed significant differences in morphology between the surfaces of the Cu plate facing the substrate (surface A) and the other surface (surface B). Figure 4 shows the SEM images of surface A of the Cu plate obtained while using these alternative substrates. These images indicate the preferential formation of thin films composed of particles with a two-dimensional morphology on surface A, clearly demonstrating a selective crystal growth in the two-dimensional microspace. However, the two-dimensional morphology differed greatly depending on the nature of the substrate used. The formation of a two-dimensional microspace using two Cu plates gave rise to thin films composed of quadrilateral nanoplates of approximately 0.8–2.4 µm (an average dimension of 1.41 µm) on each side of surface A (Figure 4a), which are similar to those (Figure 2a,b) obtained on surface A using the Al₂O₃ plate. The average thickness of the quadrilateral nanoplates, ca. 280 nm, synthesized using the Cu plate as the substrate, was slightly larger than that synthesized using the Al₂O₃ plate as the substrate (ca. 160 nm). This thickness difference is probably due to the larger number of complex ions generated by the CuO precursor in the two-dimensional microspace between the two Cu plates than between the Al₂O₃ and Cu plates. Using the SUS316L plate resulted in the synthesis of a thin film composed of thin quadrilateral nanoplates on surface A (Figure 4b). The quadrilateral nanoplates obtained using the SUS316L plate are larger and thinner than those obtained using the Al₂O₃ and Cu plates. Although SUS316L is a corrosion-resistant substance used in biomaterials, trace elements eluted from SUS316L into the NaOH solution during the hydrothermal reaction may have a slight influence on the growth of CuO crystals. The silver color of the SUS316L plate changed to brown after the reaction. The XRD patterns (Figure 3d,e) of surface A obtained using the Cu and SUS316 plates were similar to that on surface A obtained using the Al₂O₃ plate (Figure 3a), which confirmed the formation of highly crystalline CuO. Using the Ti plate resulted in thin films composed of plates of ca. 1.0 µm with bulky particles several µm or more in size (Figure 4c). The XRD patterns of this thin film (Figure 3f) revealed diffraction peaks attributed to CuO. The intensities of these diffraction peaks were markedly lower than the CuO peaks in the XRD patterns of the quadrilateral nanoplate thin film (Figure 3a,d,e), indicating the extremely low crystallinity of CuO in the plates. Ti plates are known to react with aqueous NaOH solution to form sodium titanate. In the present study, during the reaction, a large amount of Ti chemical species generated from the Ti plate adsorbed onto the CuO surface, due to which the crystal growth of CuO was inhibited to some extent and resulted in CuO plates with low crystallinity. These results suggest that by changing the nature of the substrate in the formation of the two-dimensional microspace on the surface of the Cu plate, precise control of the nanostructure of CuO thin films can be achieved.

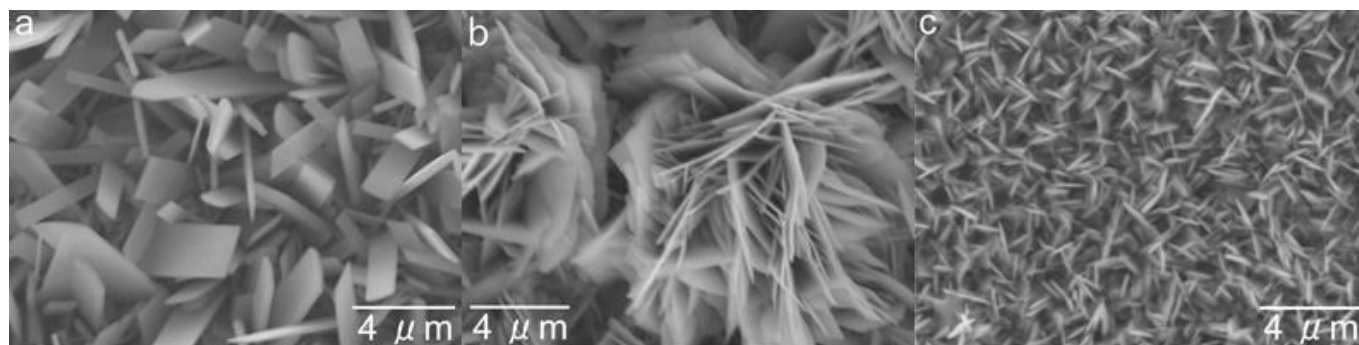


Figure 4. SEM images of thin films formed on surface A of the Cu substrates obtained using (a) Cu, (b) SUS316L, and (c) Ti plates as the substrate instead of the Al_2O_3 plate.

4. Conclusions

In the present study, the use of a two-dimensional microspace as a reaction field resulted in the successful synthesis of a thin film composed of quadrilateral CuO nanoplates on the surface of a Cu plate. This thin film combines the excellent mechanical properties and conductivity of the Cu plate, and the particular chemical properties related to the controlled morphology of the CuO quadrilateral nanoplates. Hence, this composite material has potential applications as a material for sensors, catalysts, and batteries. The synthetic strategy developed in the present study, where a two-dimensional microspace was used as a reaction field, can be applied to the synthesis of novel ceramic thin film/metal composites with a variety of tailored nanostructures.

Author Contributions: Conceptualization, M.Y. and Y.I.; methodology, Y.I.; investigation, M.Y.; resources, M.Y.; data curation, M.Y.; writing—review and editing, M.Y.; visualization, M.Y. and Y.I.; supervision, M.Y.; project administration, M.Y. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: The data presented in this study are available on request from the corresponding author.

Acknowledgments: The authors thank Seiji Otsuka for his contributions to data acquisition.

Conflicts of Interest: The authors declare no conflicts of interest.

References

1. Sun, S.; Zhang, X.; Sun, Y.; Yang, S.; Song, X.; Yang, Z. Facile Water-Assisted Synthesis of Cupric Oxide Nanourchins and Their Application as Nonenzymatic Glucose Biosensor. *ACS Appl. Mater. Interfaces* **2013**, *5*, 4429–4437. [[CrossRef](#)] [[PubMed](#)]
2. Svintsitskiy, D.A.; Kardash, T.Y.; Stonkus, O.A.; Slavinskaya, E.M.; Stadnichenko, A.I.; Koscheev, S.V.; Chupakhin, A.P.; Boronin, A.I. In Situ XRD, XPS, TEM, and TPR Study of Highly Active in CO Oxidation CuO Nanopowders. *J. Phys. Chem. C* **2013**, *117*, 14588–14599. [[CrossRef](#)]
3. Pecquenard, B.; Cras, F.L.; Poinot, D.; Sicardy, O.; Manaud, J.-P. Thorough Characterization of Sputtered CuO Thin Films Used as Conversion Material Electrodes for Lithium Batteries. *ACS Appl. Mater. Interfaces* **2014**, *6*, 3413–3420. [[CrossRef](#)] [[PubMed](#)]
4. Manna, S.; Das, K.; De, S.K. Template-Free Synthesis of Mesoporous CuO Dandelion Structures For Optoelectronic Applications. *ACS Appl. Mater. Interfaces* **2010**, *2*, 1536–1542. [[CrossRef](#)] [[PubMed](#)]
5. Nwanya, A.C.; Obi, D.; Ozoemena, K.I.; Osuji, R.U.; Awada, C.; Ruediger, A.; Maaza, M.; Rosei, F.; Ezema, F.I. Facile Synthesis of Nanosheet-like CuO Film and its Potential Application as a High-Performance Pseudocapacitor Electrode. *Electrochimica Acta* **2016**, *198*, 220–230. [[CrossRef](#)]
6. Basu, M.; Sinha, A.K.; Pradhan, M.; Sarkar, S.; Negishi, Y.; Pal, T. Fabrication and Functionalization of CuO for Tuning Superhydrophobic Thin Film and Cotton Wool. *J. Phys. Chem. C* **2011**, *115*, 20953–20963. [[CrossRef](#)]
7. Yu, X.-Y.; Xu, R.-X.; Gao, C.; Luo, T.; Jia, Y.; Liu, J.-H.; Huang, X.-J. Novel 3D Hierarchical Cotton-Candy-Like CuO: Surfactant-Free Solvothermal Synthesis and Application in As(III) Removal. *ACS Appl. Mater. Interfaces* **2012**, *4*, 1954–1962. [[CrossRef](#)] [[PubMed](#)]

8. Artioli, G.A.; Mancini, A.; Barbieri, V.R.; Quattrini, M.C.; Quartarone, E.; Mozzati, M.C.; Drera, G.; Sangaletti, L.; Gombac, V.; Fornasiero, P.; et al. Correlation between Deposition Parameters and Hydrogen Production in CuO Nanostructured Thin Films. *Langmuir* **2016**, *32*, 1510–1520. [[CrossRef](#)]
9. Lim, Y.-F.; Chua, C.S.; Lee, C.J.J.; Chi, D. Sol-gel deposited Cu₂O and CuO thin films for photocatalytic water splitting, *Phys. Chem. Chem. Phys.* **2014**, *16*, 25928–25934. [[CrossRef](#)]
10. Anandan, S.; Wen, X.; Yang, S. Room temperature growth of CuO nanorod arrays on copper and their application as a cathode in dye-sensitized solar cells. *Mater. Chem. Phys.* **2005**, *93*, 35–40. [[CrossRef](#)]
11. Zhang, W.; Ding, S.; Yang, Z.; Liu, A.; Qian, Y.; Tang, S.; Yang, S. Growth of novel nanostructured copper oxide (CuO) films on copper foil. *J. Cryst. Growth* **2006**, *291*, 479–484. [[CrossRef](#)]
12. Liu, Y.; Chu, Y.; Zhuo, Y.; Li, M.; Li, L.; Dong, L. Anion-Controlled Construction of CuO Honeycombs and Flowerlike Assemblies on Copper Foils. *Cryst. Growth Des.* **2007**, *7*, 467–470. [[CrossRef](#)]
13. Zhang, X.; Wang, G.; Zhang, W.; Hu, N.; Wu, H.; Fang, B. Seed-Mediated Growth Method for Epitaxial Array of CuO Nanowires on Surface of Cu Nanostructures and Its Application as a Glucose Sensor. *J. Phys. Chem. C* **2008**, *112*, 8856–8862. [[CrossRef](#)]
14. Jana, S.; Das, S.; Das, N.S.; Chattopadhyay, K.K. CuO nanostructures on copper foil by a simple wet chemical route at room temperature. *Mater. Res. Bull.* **2010**, *45*, 693–698. [[CrossRef](#)]
15. Ekthammathat, N.; Thongtem, T.; Thongtem, S. Antimicrobial activities of CuO films deposited on Cu foils by solution chemistry. *Appl. Surf. Sci.* **2013**, *277*, 211–217. [[CrossRef](#)]
16. Jiang, X.; Herricks, T.; Xia, Y. CuO Nanowires Can Be Synthesized by Heating Copper Substrates in Air. *Nano Letters* **2002**, *2*, 1333–1338. [[CrossRef](#)]
17. Xu, C.H.; Woo, C.H.; Shi, S.Q. Formation of CuO nanowires on Cu foil. *Chem. Phys. Lett.* **2004**, *399*, 62–66. [[CrossRef](#)]
18. Zhu, Y.W.; Yu, T.; Cheong, F.C.; Xu, X.J.; Lim, C.T.; Tan, V.B.C.; Thong, J.T.L.; Sow, C.H. Large-scale synthesis and field emission properties of vertically oriented CuO nanowire films. *Nanotechnology* **2005**, *16*, 88–92. [[CrossRef](#)]
19. Kaur, M.; Muthe, K.P.; Deshpande, S.K.; Choudhury, S.; Singh, J.B.; Verma, N.; Gupta, S.K.; Yakhmi, J.V. Growth and branching of CuO nanowires by thermal oxidation of copper. *J. Cryst. Growth* **2006**, *289*, 670–675. [[CrossRef](#)]
20. Liu, Y.; Liao, L.; Li, J.; Pan, C. From Copper Nanocrystalline to CuO Nanoneedle Array: Synthesis, Growth Mechanism, and Properties. *J. Phys. Chem. C* **2007**, *111*, 5050–5056. [[CrossRef](#)]
21. Chen, J.; Wang, K.; Hartman, L.; Zhou, W. H₂S Detection by Vertically Aligned CuO Nanowire Array Sensors. *J. Phys. Chem. C* **2008**, *112*, 16017–16021. [[CrossRef](#)]
22. Djebian, R.; Boudjema, B.; Kabir, A.; Sedrati, C. Physical characterization of CuO thin films obtained by thermal oxidation of vacuum evaporated Cu. *Solid State Sci.* **2020**, *101*, 106147. [[CrossRef](#)]
23. Chang, C.-H.; Paul, B.K.; Remcho, V.T.; Atre, S.; Hutchison, J.E. Synthesis and post-processing of nanomaterials using microreaction technology. *J. Nanopart. Res.* **2008**, *10*, 965–980. [[CrossRef](#)]
24. Zhao, C.-X.; He, L.; Qiao, S.Z.; Middelberg, A.P.J. Nanoparticle synthesis in microreactors. *Chem. Eng. Sci.* **2011**, *66*, 1463–1479. [[CrossRef](#)]
25. Zou, G.; Li, H.; Zhang, D.; Xiong, K.; Dong, C.; Qian, Y. Well-Aligned Arrays of CuO Nanoplatelets. *J. Phys. Chem. B* **2006**, *110*, 1632–1637. [[CrossRef](#)]
26. Moura, A.P.; Cavalcante, L.S.; Sczancoski, J.C.; Stroppa, D.G.; Paris, E.C.; Ramirez, A.J. Structure and Growth Mechanism of CuO Plates Obtained by Micro-wave-Hydrothermal without Surfactants. *Adv. Powder Technol.* **2010**, *21*, 197–202. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.