

Understanding the Effects of Plastic Fines as a Bitumen Modifier on the Performance Properties of Hot Mix Asphalt [†]

Idorenyin Ndarake Usanga ^{1,*} , Chijioke Christopher Ikeagwuani ²  and Edidiong Esem Ambrose ¹ 

¹ Department of Civil Engineering, Akwa Ibom State University, Ikot Akpaden 532111, Nigeria; edidiongambrose@aksu.edu.ng

² Department of Civil Engineering, University of Nigeria, Nsukka 410105, Nigeria; chijioke.ikeagwuani@unn.edu.ng

* Correspondence: idorenyinusanga@aksu.edu.ng; Tel.: +234-07039180879

[†] Presented at the 4th International Electronic Conference on Applied Sciences, 27 October–10 November 2023. Available online: <https://asec2023.sciforum.net/>.

Abstract: The mechanical properties of most asphalt binders may not be sufficient to withstand the increased load requirements experienced by flexible pavement in practice, especially in regions notorious for severe climatic conditions. This necessitated the need to often enhance the properties of asphalt binder so that it can counteract most pavement distresses, such as rutting and moisture susceptibility. In this study, economical industrial waste plastic dust (IWPD) from high-density polyethylene (HDPE) origin was used to modify base bitumen with a penetration grade of 60/70, and its effect on the moisture susceptibility and rutting potential of hot-mix asphalt (HMA) was investigated thereafter. The IWPD was added at varying percentages (3%, 6%, and 9%) to the base bitumen by weight of the optimum bitumen content. Afterward, Marshall stability and indirect tensile strength ratio were performed on HMA samples produced with the IWPD-modified bitumen blends to evaluate, respectively, its rutting and moisture susceptibility. Based on the results obtained from the analysis, it was found that the modified blends of bitumen enhance the properties of the conventional bitumen. More importantly, the modified blend of bitumen with 6% IWPD content gave optimal results in terms of the increment of rutting resistance and improvement of moisture susceptibility of HMA.

Keywords: flexible pavement; industrial waste plastic dust; hot-mix asphalt; moisture susceptibility; rutting; tensile strength ratio



Citation: Usanga, I.N.; Ikeagwuani, C.C.; Ambrose, E.E. Understanding the Effects of Plastic Fines as a Bitumen Modifier on the Performance Properties of Hot Mix Asphalt. *Eng. Proc.* **2023**, *56*, 55. <https://doi.org/10.3390/ASEC2023-15394>

Academic Editor: Simeone Chianese

Published: 27 October 2023



Copyright: © 2023 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Proper asphalt mixture design is paramount for ensuring the durability as well as the stability of flexible pavements, especially considering the increasing traffic volumes resulting from population growth. Continuous exposure to heavy traffic and repetitive loading has a detrimental effect on the rheological properties and overall performance of flexible pavements. Bitumen, an essential component of asphalt concrete in flexible pavements, acts as the binding material and consists of hydrocarbons that significantly influence the performance of bituminous pavements [1]. Hence, the use of poorly characterized binder mixtures in hot-mix asphalt (HMA) exposes the flexible pavement to various distresses that can compromise its integrity [1,2]. These inadequately characterized binders contribute to several types of pavement failures, with fatigue cracking, rutting, and moisture susceptibility being extensively studied, particularly in Nigeria [3].

Rutting is a longitudinal surface depression that occurs along the wheel paths in most flexible pavements. It is an incremental permanent strain or plastic deformation that is generated in poorly designed and constructed flexible pavement during repetitive traffic loading [4–6]. It is followed subsequently by conspicuous upheaval along the sides of the rut, fatigue cracking, and surface loss, hence decreasing pavement life [7,8]. Moisture

susceptibility, which is associated with the presence of moisture in the pavement, affects asphalt mixture strength and accelerates several modes of failure such as rutting, raveling, stripping, bleeding, and cracking in asphalt pavement [9], which, in turn, escalate maintenance costs [8,10,11]. Strategies to improve this failure mode, involve the incorporation of modifiers into the asphalt binders [12–15]. While most polymer-modified binders are known to improve performance, they are expensive and hard to find, which makes the production cost of the binders modified with them to be high [16,17], and availability challenges have led to the exploration of industrial-based modifiers like polymer-based waste [18–21].

Industrial waste, a significant global concern, prompts the exploration of sustainable solutions. In Nigeria, polymer-based industrial waste poses disposal challenges due to depleting landfills amid urbanization [22]. Incorporating such waste into pavement construction can alleviate environmental impacts and resource depletion [23,24]. This study focuses on utilizing polymer-based industrial waste to improve asphalt mixture properties, particularly using high-density polyethylene (HDPE) waste. HDPE-modified asphalt has demonstrated enhanced rutting resistance and moisture susceptibility mitigation [18].

This research assesses the potential of industrial waste plastic dust (IWPD), generated during HDPE plastic manufacturing, to enhance bitumen properties, focusing on rutting resistance and moisture susceptibility.

2. Materials and Method

2.1. Materials

This study used 60/70 penetration grade bitumen from Ringardas Nigeria Limited. Its properties are presented in Table 1. Crushed granite stone and dust obtained from a quarry in Akamkpa, Cross River State, were utilized as coarse aggregate and mineral fillers, respectively, while natural sand obtained from a river in Ikot Osom, Akwa Ibom State, was used as fine aggregate. Figure 1 and Table 2 display, respectively, the gradation curve and the physical properties of the aggregates used in this study. The physical properties were all determined based on American Society for Testing and Materials standards procedures.

Table 1. Physical properties of base bitumen.

Test	60/70 Value	Standard Requirement
Penetration at 25 °C (0.1 mm)	67	60–70
Softening point (°C)	48.5	min 46
Brookfield rotational viscosity at 135 °C (Pa·s)	0.56	<3000 mPa·s
Flash Point (°C)	250	min 230
Specific gravity (g/cm ³)	1.02	1.01–1.06

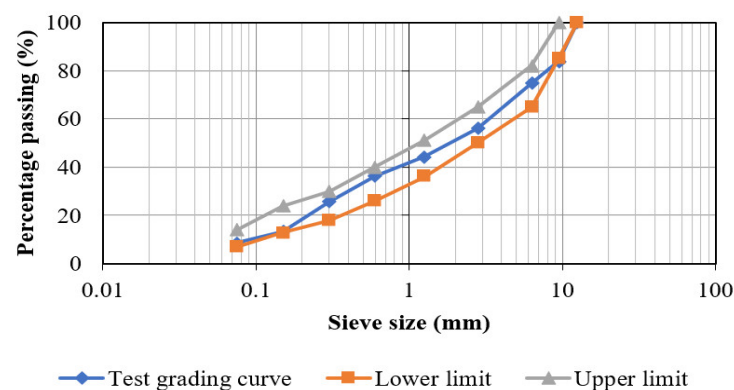


Figure 1. Aggregate gradation curve.

Table 2. Physical properties of aggregate.

Aggregate	Test	Value	Standard Requirement
Coarse aggregate	Water absorption	1.99	≤2%
	Loss Angeles abrasion	23.9	<30%
	Apparent specific gravity	2.66	2.6–2.9
Fine aggregate	Apparent specific gravity	2.61	2.5–2.8
	Water absorption	2.78	≤2%
Filler	Apparent specific gravity	2.70	2.5–2.8

HDPE plastics from Dakkada in dust form were used as IWPD. It was sourced from a plastic company in Akwa Ibom, Nigeria, that produces HDPE household items. See Table 3 for IWPD properties and Figure 2 for its appearance.

Table 3. Physical properties of IWPD.

Test	Value	Standard Requirement	Standard Adopted
Melting Temperature	130 °C	255 °C	ASTM D3418 [25]
Density	0.9439 kg/m ³	0.88–0.96 kg/m ³	ASTM D4883 [26]
Melt Flow Index	19.8 g/10 min	-	ASTM D1238 [27]

**Figure 2.** IWPD modifier.

2.2. Method

2.2.1. Preparation of IWPD—Modified Blend

Modified bitumen blends were produced by thoroughly mixing base bitumen and IWPD in a wet process in a high-shearing mixer at 160 °C and 3800 rpm for 40 min, with IWPD added at 3%, 6%, and 9% of optimal bitumen content of 5.35%

2.2.2. Indirect Tensile Strength and Tensile Strength Ratio

This study employed the indirect tensile strength (ITS) test, assessing asphalt mixture tensile properties linked to rutting and cracking using ASTM D6931 [28] and AASHTO-T283 [29] procedures. Six cylindrical specimens each for unmodified and modified blends were prepared, with three of the specimens conditioned as described in the AASHTO-T283 [29]. Specimens underwent compressive force application along the diametrical plane at a stable deformation rate until failure, calculating ITS using Equation (1) for both types.

$$ITS = \frac{2L_s}{\pi t_s d_s} \quad (1)$$

where ITS is (Pa), L_s represents the maximum applied load on specimen (N), t_s represents the thickness of specimen (mm), and d_s = diameter of specimen (mm).

Tensile strength ratio (TSR), assessing moisture damage resistance, was calculated using the ratio of conditioned (wet) to unconditioned (dry) indirect tensile strength according to Equation (2).

$$\text{TSR} = \frac{\text{ITS}_{\text{wet}}}{\text{ITS}_{\text{dry}}} \quad (2)$$

where TSR is the tensile strength ratio, ITS_{wet} is the indirect tensile strength at wet conditions, and ITS_{dry} is the tensile strength at dry conditions.

3. Result and Discussion

Tensile Strength Ratio

Figure 3 displays unconditioned and conditioned ITS for modified and unmodified bitumen blends. Unconditioned and conditioned ITS increase with higher IWPDP content. The unmodified asphalt mixture had dried and wet ITS of 0.9 MPa and 0.65 MPa. Figure 4 shows the TSR results, revealing rising TSR with increased IWPDP content. Blends with 6% and 9% IWPDP achieved the highest TSR of 81%, indicating significant moisture damage resistance, meeting super-pave standards. Beyond 6% IWPDP, marginal TSR differences are observed, attributed to increased viscosity and improved asphalt-aggregate adhesion, reducing moisture susceptibility [30].

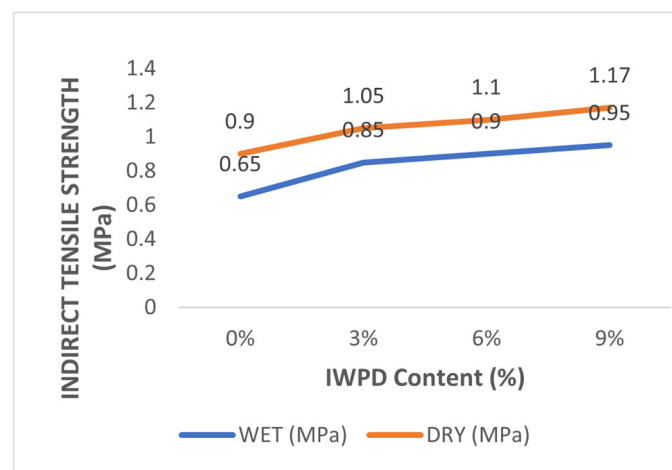


Figure 3. Indirect tensile strength at various percentages of base and modified bitumen.

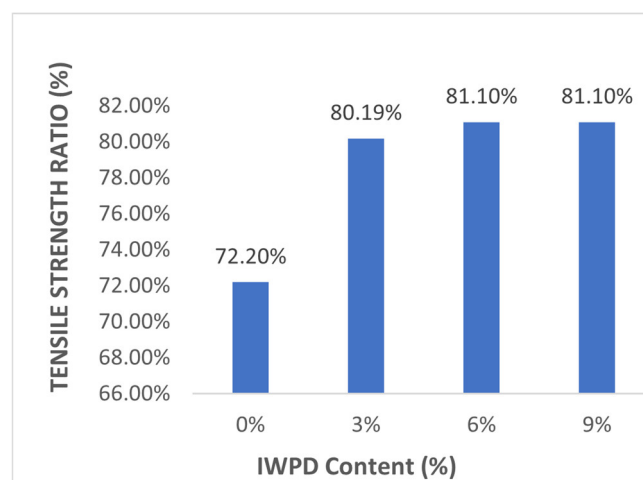


Figure 4. Tensile strength ratio of base and IWPDP modified bitumen at various percentages.

4. Conclusions

Improvement in asphalt mixtures to resist pavement distresses like rutting and moisture susceptibility can be achieved using industrial waste plastic dust as a bitumen modifier. In the present study, the following conclusions can be drawn:

1. Based on tensile strength ratio analysis, the modification of bitumen with IWPD improved moisture susceptibility. However, beyond 6% IWPD, there might be no significant improvement in moisture susceptibility. Therefore, 6% modification content may be deemed desirable.
2. The modification of bitumen with IWPD led to an improvement in the rutting potential of the asphalt mixture. Although at content beyond 6%, resistance to rutting might be reduced. Hence, like in the case of moisture susceptibility, the optimal performance of IWPD for rutting improvement might be effective at 6% by weight of bitumen.

Author Contributions: All authors contributed immensely to the study in conceptualization, methodology, analysis, validation, and manuscript writing. Formal analysis of laboratory outcome was jointly carried out by all the authors, I.N.U., C.C.I. and E.E.A. Conceptualization of the work, laboratory investigations, results analysis, and writing of the first draft of the manuscript was performed by I.N.U. Laboratory investigation, data analysis, and substantial technical contribution in reviewing and editing the work were performed by C.C.I. Laboratory investigation, data analysis, and vetting of the draft manuscript were performed by E.E.A. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: All data generated and analyzed during this study are included in the published article.

Acknowledgments: The authors acknowledge support from Cafmeg Laboratory, Shelter Afrique, Nigeria, for allowing the use of their laboratory in conducting this research.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Little, D.N.; Jones, D.R. Moisture sensitivity of Asphalt pavements: Chemical and Mechanical Processes of Moisture Damage in Hot—Mix Asphalt Pavements. In *National Seminar on Moisture Sensitivity of Asphalt Pavements*; Transportation Research Board: San Diego, CA, USA, 2003.
2. Ikeagwuani, C.C.; Nwonu, D.C.; Nweke, C.C. Resilient modulus descriptive analysis and estimation for fine-grained soils using multivariate and machine learning methods. *Int. J. Pavement Eng.* **2021**, *23*, 3409–3424. [\[CrossRef\]](#)
3. Li, Y.; Hao, P.; Zhao, C.; Ling, J.; Wu, T.; Li, D.; Liu, J.; Sun, B. Anti-rutting performance evaluation of modified asphalt binders: A review. *J. Traffic Transp. Eng.* **2021**, *8*, 339–355. [\[CrossRef\]](#)
4. Kandhal, P.; Cooley, L. *Accelerated Laboratory Rutting Test: Evaluation of the Asphalt Pavement Analyzer*; Transportation Research Board: Washington, DC, USA, 2003.
5. Qadir, A.; Gazder, U.; Chouhary, K. Statistical analysis for comparing and predicting rutting resistance of asphalt pavements with rigid and flexible geogrid layers. *Constr. Build. Mater.* **2021**, *302*, 124136. [\[CrossRef\]](#)
6. Mirabdolazimi, S.; Shafabakhsh, G. Rutting depth prediction of hot mix asphalts modified with forta fiber using artificial neural networks and genetic programming technique. *Constr. Build. Mater.* **2017**, *148*, 666–674. [\[CrossRef\]](#)
7. Chilukwa, N.; Lungu, R. Determination of Layers Responsible for Rutting Failure in a Pavement Structure. *Infrastructures* **2019**, *4*, 29. [\[CrossRef\]](#)
8. Baghaee, M.; Soltani, M.; Karim, M. Evaluation of permanent deformation characteristics of unmodified and Polyethylene Terephthalate modified asphalt mixtures using dynamic creep test. *Mater. Des.* **2014**, *53*, 317–324. [\[CrossRef\]](#)
9. Usanga, I.N.; Okafor, F.O.; Ikeagwuani, C.C. Investigation of the Performance of Hot Mix Asphalt Enhanced with Calcined Marl Dust Used as Fillers. *Int. J. Pavement Res. Technol.* **2023**. [\[CrossRef\]](#)
10. Zhang, Y.; Ling, M.; Kaseer, F.; Arambula, E.; Lyttin, R.L.; Matin, A.E. Prediction and evaluation of rutting and moisture susceptibility in rejuvenated asphalt mixtures. *J. Clean. Prod.* **2022**, *33*, 129980. [\[CrossRef\]](#)
11. Brown, E.; Kandhal, P.A.Z.J. *Performance Testing for Hot Mix Asphalt*; National Center for Asphalt Technology (NCAT): Auburn, Alabama, 2001.

12. Kalantar, Z.N.; Karim, M.R.; Mahrez, A. A review of using waste and virgin polymer in pavement. *Constr. Build. Mater.* **2012**, *33*, 55–62. [[CrossRef](#)]
13. Dalhat, M.A.; Wahhab, H.I.A.-A. Performance of recycled plastic waste modified asphalt binder in Saudi Arabia. *Int. J. Pavement Eng.* **2017**, *18*, 349–357. [[CrossRef](#)]
14. Polacco, G.; Filippi, S.; Merusi, F.; Stastna, G. A review of the fundamentals of polymer-modified asphalts: Asphalt/polymer interactions and principles of compatibility. *Adv. Colloid Interface Sci.* **2015**, *224*, 72–112. [[CrossRef](#)] [[PubMed](#)]
15. Usanga, I.; Ikeagwuani, C.; Etim, R.; Attah, I. Predictive Modelling of Modified Asphalt Mixture Rutting Potentials: Machine Learning Approach. *Iran. J. Sci. Technol. Trans. Civ. Eng.* **2023**, *47*, 4087–4101. [[CrossRef](#)]
16. Adhikari, B.; Maiti, D.D. Reclamation and recycling of waste rubber. *Prog. Polym. Sci.* **2000**, *25*, 909–948. [[CrossRef](#)]
17. Becker, Y.; Mendez, M.P.; Rodriguez, Y. Polymer modified asphalt. *Vis. Technol.* **2001**, *9*, 39–48.
18. Hınıslıoglu, S.; Agar, E. Use of waste high density polyethylene as bitumen modifier in asphalt concrete mix. *Mater. Lett.* **2004**, *58*, 267–271. [[CrossRef](#)]
19. García-Morales, M.; Partal, P.; Navarro, F.; Gallegos, C. Effect of waste polymer addition on the rheology of modified bitumen. *Fuel* **2006**, *85*, 936–943. [[CrossRef](#)]
20. Kumar, P.; Garg, R. Rheology of waste plastic fibre-modified bitumen. *Int. J. Pavement Eng.* **2011**, *12*, 449–459. [[CrossRef](#)]
21. Obaid, H.A. Characteristics of warm mixed asphalt modified by waste polymer and nano-silica. *Int. J. Pavement Res. Technol.* **2021**, *14*, 397–401. [[CrossRef](#)]
22. Aderogba, K. Polymer wastes and Management in Cities and Towns of Africa and Sustainable Environment: Nigeria and European Experiences. *Soc. Sci.* **2014**, *3*, 79–88.
23. Torres, H.P.; Fernandes, S.R.; Loureiro, C.D.; Moura, C.F.; Silva, H.M.; Oliveira, J.R. Use of polymer modified binders as rejuvenators in recycled asphalt mixtures. *Int. J. Pavement Res. Technol.* **2020**, *13*, 654–664. [[CrossRef](#)]
24. Ikeagwuani, C.C.; Nwonu, D.C. Variable returns to scale DEA-Taguchi approach for ternary additives in expansive soil subgrade. *Int. J. Geo-Eng.* **2021**, *12*, 20. [[CrossRef](#)]
25. ASTM D3418; American Society for Testing and Materials, Standard Test Method for Transition Temperatures and Enthalpies and Fusion Crystallization of Polymers by Differential Scanning Calorimetry. ASTM: West Conshohocken, PA, USA, 2021.
26. ASTM D4883; American Society for Testing and Materials, Standard Test Method for Density of Polyethylene by the Ultrasound Technique. ASTM: West Conshohocken, PA, USA, 2018.
27. ASTM D1238; American Society for Testing and Materials, Standard Test Method for Melt Flow Rates of Thermoplastic by Extrusion Plastomer. ASTM: West Conshohocken, PA, USA, 2013.
28. ASTM D6931; American Society for Testing and Materials, Standard Test Method for Indirect Tensile (DT) Strength of Bituminous Mixtures. ASTM: West Conshohocken, PA, USA, 2012.
29. AASHTO-T283; American Association of State Highway and Transportation Officials, Standard Method of Test for Resistance of Compacted Asphalt Mixtures to Moisture-Induced Damage. AASHTO: Washington, DC, USA, 2022.
30. Hasan, E.A.; Abed, Y.H.; Al-Haddad, A.H.A. Improved Adhesion Bond between Asphalt Binder-Aggregate as Indicator to Reduced Moisture Damage. *J. Phys. Conf. Ser.* **2021**, *1973*, 012059. [[CrossRef](#)]

Disclaimer/Publisher's Note: The statements, opinions and data contained in all publications are solely those of the individual author(s) and contributor(s) and not of MDPI and/or the editor(s). MDPI and/or the editor(s) disclaim responsibility for any injury to people or property resulting from any ideas, methods, instructions or products referred to in the content.