

# Effect of Milling Time on the Sensing Properties of Fly Ash Zeolite Composite Thin Films <sup>†</sup>

Katerina Lazarova <sup>1,\*</sup>, Silviya Boycheva <sup>2</sup> , Marina Vasileva <sup>1</sup>, Denitza Zgureva <sup>3</sup>  and Tsvetanka Babeva <sup>1,\*</sup> 

<sup>1</sup> Institute of Optical Materials and Technologies “Acad. J. Malinowski”, Bulgarian Academy of Sciences, Acad. G. Bonchev Str., bl. 109, 1113 Sofia, Bulgaria; marina@iomt.bas.bg

<sup>2</sup> Department of Thermal and Nuclear Power Engineering, Technical University of Sofia, 8 Kl. Ohridsky Blvd, 1000 Sofia, Bulgaria; sboycheva@tu-sofia.bg

<sup>3</sup> College of Energy and Electronics, Technical University of Sofia, 8 Kl. Ohridsky Blvd, 1000 Sofia, Bulgaria; dzgureva@gmail.com

\* Correspondence: klazarova@iomt.bas.bg (K.L.); babeva@iomt.bas.bg (T.B.); Tel.: +359-02-979-3521 (K.L.)

<sup>†</sup> Presented at the 8th International Symposium on Sensor Science, 17–28 May 2021; Available online: <https://i3s2021dresden.sciforum.net/>.

**Abstract:** Thin films, consisting of a sol–gel Nb<sub>2</sub>O<sub>5</sub> matrix doped with zeolite Na-X synthesized from fly ash through ultrasonic-assisted double-stage fusion-hydrothermal alkaline activation, were deposited by the spin-coating method. In order to improve the optical quality and sensing properties of the thin films, zeolites were wet milled for 60, 120 and 540 s prior to incorporation in the film. The liquid adsorption ability of thin films was tested by measuring the reflectance spectra prior to and after exposure to liquid acetone and the change in the reflection coefficient  $\Delta R$  of the films was calculated. The influence of milling time of zeolites on the sensing and optical properties of the films was studied.

**Keywords:** optical sensor; sol–gel; Nb<sub>2</sub>O<sub>5</sub>; thin films; zeolites; fly ash



**Citation:** Lazarova, K.; Boycheva, S.; Vasileva, M.; Zgureva, D.; Babeva, T. Effect of Milling Time on the Sensing Properties of Fly Ash Zeolite Composite Thin Films. *Eng. Proc.* **2021**, *6*, 55. <https://doi.org/10.3390/I3S2021Dresden-10068>

Academic Editors: Gianauelio Cuniberti and Larysa Baraban

Published: 17 May 2021

**Publisher's Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Copyright:** © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

Adding zeolites to a metal oxide matrix is one possible way to increase overall porosity when deposited in the form of thin films [1]. In addition to the intrinsic microporosity of the zeolites, it is also possible for additional free volume (air) to be introduced into the samples with different volume fractions, depending on the concentration and size of the zeolite particles [2]. An example of rare natural zeolites is Faujasite (FAU) and its synthetic sodium form - Na-X, which is widely used because of its structural super-cage, large pore size and high specific surface area [3]. Zeolite Na-X can be obtained by utilizing waste aluminosilicates, including fly ash (FA), from coal combustion. FA, generated as a by-product in the energy production from coal-fired Thermal Power Plants (TPP), typically contains above 70 wt. % of amorphous and crystalline aluminosilicates [4]. Different synthesis approaches have been studied for the conversion of FA to zeolites, among which the atmospheric crystallization, alkaline hydrothermal activation, and double-stage fusion-hydrothermal synthesis have been considered as the most technologically viable. Zeolite Na-X, which crystallizes as a metastable phase upon alkaline activation of FA, can be obtained by all three synthesis techniques. However, the highest degree of conversion of raw FA to a single Na-X phase is achieved by applying two-stage synthesis. The high-temperature alkaline fusion stage preceding the hydrothermal synthesis facilitates the conversion of the resistant crystalline phases from the FA composition, such as quartz, mullite and anorthite in soluble alkaline silicates and aluminates and their assimilation in the final product. When ultrasonic treatment is applied for homogenization of the reaction mixture between the fusion and hydrothermal stages, a nanocrystalline structure of the obtained zeolite Na-X is achieved with fine distribution in the zeolite matrix of the iron

oxides transferred from the raw FA [5]. Moreover, the ultrasonic fragmentation of the crystallization seeds increases the external surface of the zeolite particles, which is essential for their application as sensor materials.

In this paper, the effect of zeolites milling time on optical and sensing properties of  $\text{Nb}_2\text{O}_5$  thin films doped with Na-X zeolites, synthesized from coal fly ash was studied. Zeolites were wet-milled for 60, 120 and 540 s prior to the incorporation in the sol-gel matrix in order to achieve different levels of porosity. Optical and sensing properties were studied through reflectance measurements before and after exposure to testing analyte (liquid acetone in this case).

## 2. Materials and Methods

FA was sampled from the electrostatic precipitators of the lignite coal supplied TPP “AES Galabovo” in Bulgaria in order to be utilized for the synthesis of zeolite Na-X. Powder samples were synthesized by ultrasonic-assisted double stage fusion-hydrothermal alkaline conversion and were studied with respect to their phase composition, morphology and surface properties [6]. Zeolite powders were subjected to wet ball milling with a PULVERISETTE 23 Mini-Ball Mill (FRITSCH) for 60, 120 and 540 s and 50 osc/min, as 0.08 g of Na-X powder were added to 3 mL distilled water.


For the deposition of metal oxide thin films, 0.010 mL zeolites from the milled water solution was mixed with 0.030 mL of ethanol and then added to 0.190 mL Nb sol [7].

Thin  $\text{Nb}_2\text{O}_5$ -Na-X films were deposited by spin-coating at a rate of 4000 rpm for 60 s by dropping 0.3 mL of the sol/zeolite solution on pre-cleaned Si substrates. After deposition, the films were annealed in air at 320 °C for 30 min. The thickness and optical constants (refractive index  $n$  and extinction coefficient  $k$ ) were determined from the measured reflectance spectra of the films at a normal light incidence using a non-linear curve-fitting method [8]. In order to study sensing properties of the films, reflectance spectra were measured prior to and after exposure to liquid acetone using 3D Optical profiler, Zeta-20, Zeta Instruments.

## 3. Results and Discussion

The measured reflectance spectra  $R$  of all thin films are similar, but the calculations of the thickness  $d$  showed that an increase in milling time leads to a decrease of  $d$  from 38.0 nm (60 s) to 35 nm (540 s), while the refractive index  $n$  of the films increases from 1.72 to 1.83, respectively. Extinction coefficient  $k$  showed no change with milling time of zeolites—0.019.

The liquid adsorption ability of thin Na-X films was tested by measuring the reflectance spectra prior to and after exposure to liquid acetone and the change in the reflection coefficient  $\Delta R$  of the films was calculated. Figure 1 shows reflectance spectra  $R$  measured in air (blue curve) and after exposure to liquid acetone (green curve) for the thin film doped with zeolites milled for 60 s.

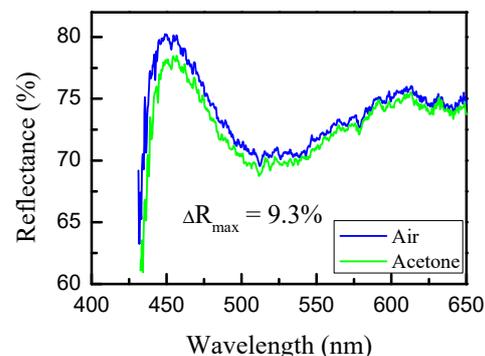

**Figure 1.** Reflectance spectra  $R$  in air (blue line) and after exposure to liquid acetone (green line) for  $\text{Nb}_2\text{O}_5$  thin film doped with fly ash zeolites milled for 60 s.

Maximum change in R is observed for milling time of 60 s— $\Delta R = 9.3\%$  for wavelength 435 nm. The increase in milling time to 540 s leads to a decrease of reflectance change  $\Delta R$  almost twice. One possible reason for this is the decrease in the proportion of micro and mesopores with increasing grinding time.

#### 4. Conclusions

The successful deposition of composite thin films comprising  $\text{Nb}_2\text{O}_5$  matrix and fly ash Na-X zeolites milled for 60 s, 120 s and 540 s is demonstrated. An increase in the refractive index with an increase in the milling time of zeolites is observed, probably due to decrease in the thickness of the composite films or a decrease in porosity. Different levels of porosity are obtained and confirmed by reflectance measurements of the films before and after exposure to acetone in liquid state. The measured reflectance change decreases with the increasing milling time of the zeolites. The greatest liquid-induced change in R is observed for thin film samples doped with zeolites milled for 60 s—9.3%.

**Author Contributions:** Conceptualization, K.L., T.B. and S.B.; methodology, K.L. and T.B.; software, K.L. and T.B.; validation, K.L., T.B. and S.B.; formal analysis, K.L., D.Z. and M.V.; investigation, K.L., D.Z. and M.V.; resources, S.B. and T.B.; writing—original draft preparation, K.L.; writing—review and editing, K.L., T.B. and S.B. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research received no external funding.

**Institutional Review Board Statement:** Not applicable.

**Informed Consent Statement:** Not applicable.

**Data Availability Statement:** Not applicable.

**Acknowledgments:** The financial support of Bulgarian National Science Fund (BNSF) under the project DN 17/18 (12 December 2017) is highly appreciated. Research equipment of Distributed Research Infrastructure INFRAMAT, part of Bulgarian National Roadmap for Research Infrastructures, supported by Bulgarian Ministry of Education and Science was used in this investigation.

**Conflicts of Interest:** The authors declare no conflict of interest.

#### References

1. Lazarova, K.; Awala, H.; Fallah, J.; Vasileva, M.; Mintova, S.; Babeva, T. Optimization of optical and sensing properties of sol-gel oxides through zeolite doping. *Bulg. Chem. Commun.* **2017**, *49*, 88–94.
2. Lazarova, K.; Boycheva, S.; Vasileva, M.; Zgureva, D.; Babeva, T. Influence of the Size of Coal Ash FAU Zeolites Used as Dopants on the Sensing Properties of  $\text{Nb}_2\text{O}_5$  Thin Films. *Mater. Proc.* **2020**, *2*, 682. [[CrossRef](#)]
3. Goldyn, K.; Anfray, C.; Komaty, S.; Ruaux, V.; Hélaine, C.; Retoux, R.; Valable, S.; Valtchev, V.; Mintova, S. Copper exchanged FAU nanozeolite as non-toxic nitric oxide and carbon dioxide gas carrier. *Microporous Mesoporous Mater.* **2019**, *280*, 271–276. [[CrossRef](#)]
4. Boycheva, S.; Zgureva, D.; Lazarova, H.; Popova, M. Comparative studies of carbon capture onto coal fly ash zeolites Na-X and Na–Ca-X. *Chemosphere* **2021**, *271*, 129505. [[CrossRef](#)] [[PubMed](#)]
5. Boycheva, S.; Marinov, I.; Miteva, S.; Zgureva, D. Conversion of coal fly ash into nanozeolite Na-X by applying ultrasound assisted hydrothermal and fusion-hydrothermal alkaline activation. *Sustain. Chem. Pharm.* **2020**, *15*, 100217. [[CrossRef](#)]
6. Popova, M.; Boycheva, S.; Lazarova, H.; Zgureva, D.; Lázár, K.; Szegedi, Á. VOC oxidation and  $\text{CO}_2$  adsorption on dual adsorption/catalytic system based on fly ash zeolites. *Catal. Today* **2020**, *357*, 518–525. [[CrossRef](#)]
7. Arfsten, N.J.; Gavlas, J.F. Niobium Oxide-Based Layers for Thin Film Optical Coatings and Processes for Producing the Same. U.S. Patent US6811901B1, 2 November 2004.
8. Lazarova, K.; Vasileva, M.; Marinov, G.; Babeva, T. Optical characterization of sol-gel derived  $\text{Nb}_2\text{O}_5$  thin films. *Opt. Laser Technol.* **2014**, *58*, 114–118. [[CrossRef](#)]